

Synthesis and characterization of a high surface area activated carbon derived from cassava peels waste by KOH activation

T.E Amakoromo, J.A Amusan, O.E Abumere

ABSTRACT

This work presents the synthesis of activated carbon, a very important material with lots of use cases in textile, food industries and even in energy storage as an electrode material in supercapacitor development. Abundantly available cassava peels was used as a raw material for the production of the activated carbon by adopting the chemical activation approach which utilized KOH as activating agent. The activation was carried out at 800°C in a tubular furnace. Scanning electron micrographs (SEM) showed that a highly porous carbon structure was achieved with high specific surface area of 828m²g⁻¹ as evident from the BET results. Raman spectrophotometer analysis showed that the prepared activated carbon was highly graphitized as seen from the G peak. The existence of mesopores and micropores was confirmed by the N₂ adsorption/desorption analysis which also revealed the presence of a hysteresis loop and a P/P₀=0.45 value.

Keywords: [Activated carbon, Cassava peels, Chemical Activation, Energy storage, Materials, Porous carbon, Surface area]

1 INTRODUCTION

Activated carbons are widely explored in many fields due to their inherent properties which are good porosity and surface area. These properties make them serve as excellent adsorbents in the removal of pollutants and purification in both gaseous and liquid media [1]. Amongst other industries, the textile, electroplating and food industries regularly discharge colored waste water and effluents which if left untreated pose life threatening risks to the environment due to their toxicity.

Treatment by biological means, coagulation, oxidation, membrane filtration and adsorption are some of the most commonly used techniques for these effluents. Of all these methods adsorption is most adopted perhaps due to its ability to remove even color from the pollutant and activated carbon is arguably the most widely used for its adsorbent properties [2].

Another growing field of application of activated carbon is the renewable energy field, where lack of proper energy storage systems have continually hampered the switch from commonly used energy systems (fossils) to their renewable counterpart. With the advent of electric vehicles and electronic devices becoming more portable, efficient energy storage devices have become very important. Batteries have long played this role but for their poor power densities, reliance is now shifted to the Electrochemical Double Layer capacitors (EDLC) otherwise known as supercapacitors due to their high power densities and long cyclability [3].

EDLC electrodes can be easily made from activated carbon and this has opened up another broad research area to not only make the activated carbon produced for this purpose


environmentally friendly, but also very cheap and readily available[4]. The catch in this interest is the porosity, good electrical conductivity and electrical stability of activated carbon and the high carbon content which is suitable for energy storage [5].

Preparation of commercially available activated carbons actually go through a whole lot of complicated procedures which pose the risk of keeping the developing countries behind in application [6]. For this reason, an easy approach and abundance based method is suggested. Using easily assessable biomass as starting materials will prove cost effective and show availability at all times. So many biomass has been reportedly used in the preparation of activated carbon. Materials such bamboo [7], olive stones [8], nipa palm nut [1], corncob [9], rice husk[10] and hydrochar [11] have all been used to produce activated carbon. using the two main methods of activation reported by Sevilla and Mokaya (2018).

There are two main approaches to preparation of activated carbon; chemical activation and physical activation. Physical Activation utilizes a process whereby carbonaceous material is carbonized which is followed by an activating process in the presence of steam or CO₂. This is done at elevated temperatures where the precursor is made to have contact with the gas or steam for activation [12]. In physical activation, the processes of carbonization and activation are two separate processes. In Chemical activation, the precursor is impregnated with activating agent (ZnCl₂, H₃PO₄, KOH) which then undergoes heat-treatment in an inert environment. In this method, the activation and carbonization occur simultaneously and at lower temperatures when compared to the physical activation process, leading to better pore structure

development in the carbon material [13]. Physical activation produces carbons with porous structures made up of mostly micropores (<2nm), while chemical activation produces more versatile materials having larger surface area, with porosities made up of mesopores and micropores. In this study, cassava peels is used as precursor in the production of activated carbon by chemical activation using KOH as activating agent as seen in Scheme 1. Cassava is

by far the most abundant agricultural produce in Nigeria which appears in various forms of food in every household across the country. However, its peels poses grave challenge to the environment as an agricultural waste and disposal is always a challenge. Recycling these wastes to a useful venture will be of high economic and research importance to the nation.

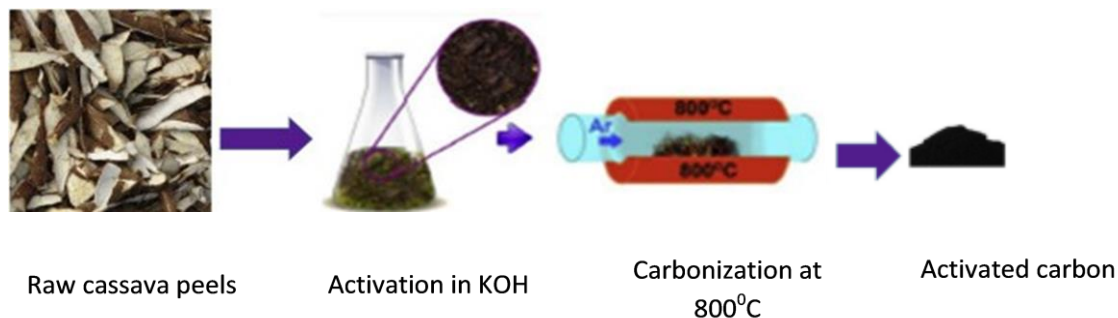

Scheme 1: Production of activated carbon from cassava peels

2 MATERIALS AND METHODS

2.1 Preparation and Synthesis of Activated Carbon from Cassava Peels

Freshly uprooted cassavas were collected from local farmers in the sub-urban Abuja, Nigeria. The peels were continuously washed until all forms of dirt were removed and subsequently oven dried for 12 hours at 60°C. The dried samples were then first crushed with a jaw crusher and further ball-milled to achieve fine powder form. Approximately 3g of the carbon precursor (cassava peels) was measured and poured into a mortar together with 12g of KOH pellets (1:4 ratio) and mixed to form a uniform powder. The mixture was then carbonized under Nitrogen gas flow in a Carbolite tube furnace at 800°C at a 5°Cmin⁻¹ heating rate and left to carbonize for one hour. The activated carbon was then removed from the furnace tube, allowed to cool to room temperature and washed with 1M HCl to remove any inorganic salts and then washed with distilled water continuously until a Neutral pH was achieved. The sample was finally oven-dried for 24 hours at 80°C.

2.2 Proximate analysis

Proximate analysis of cassava peel showed that the moisture content, fixed carbon, ash content, and the volatile

matter were 4.5%, 80.53%, 5.28% and 9.62% respectively as represented in table 1.

2.3 Physico-chemical Analysis

An X-Pert Pro instrument was used to carry out X-ray diffraction (XRD) studies of the activated carbon samples, with a reflection geometry of 2θ values (10-80°) and a radiation (Cu- Kα) source having a 0.15418nm wavelength (λ). Also, using a Jobin Yvon Horiba TX 6400 Raman spectrophotometer, Raman spectroscopy analysis was carried out at a 15mW power rating to avoid overheating of the sample. A Zeiss Model EVO LS10 Scanning Electron Microscope was used for SEM analysis of the prepared materials to get further insight on the structure of the samples. Adsorption properties of the prepared activated carbon material were studied by adopting Nitrogen adsorption/desorption techniques using a NOVATOUGH gas adsorption analyzer. To achieve this, the samples were first degassed for 6hrs in a high vacuum environment at 100°C. Furthermore, the specific surface area of the samples was evaluated using the globally adopted BET (Brunauer-Emmett-Teller) method and the pore size distribution was subsequently determined by adopting the BJH (Barrett Joyner-Halenda) method.

Table 1: Proximate analysis of sample.

Moisture content	Fixed carbon	Ash content	Volatile matter
4.57%	80.53%	5.28%	9.62%

3 RESULTS AND DISCUSSION

Table 2: EDS elemental composition of carbon activated with KOH

Sample	C	Na	Si	Mo	S	Ca
KOH Activated	87.19	-	0.5	7.61	0.01	4.68

Table 3: BET surface area and porous textual data obtained for cassava peel derived carbon material activated at 800°C.

Sample	KOH activated cassava peels
BET (m^2g^{-1})	828
Micropore volume (cm^3g^{-1})	0.3981
Pore diameter (nm)	2.66

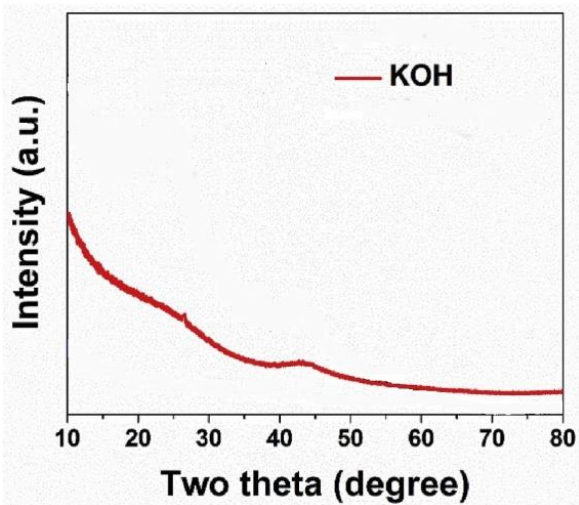


Figure 1: XRD analysis of activated carbon samples

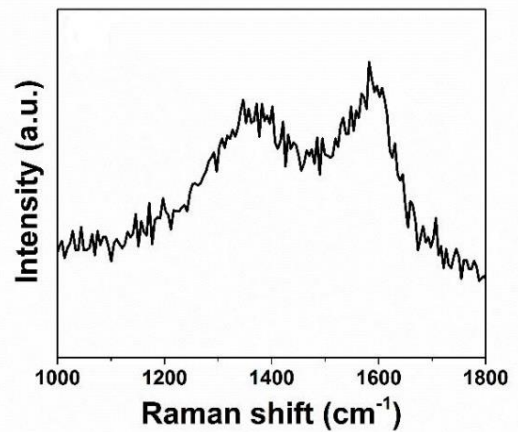


Figure 2: Raman spectra of the sample

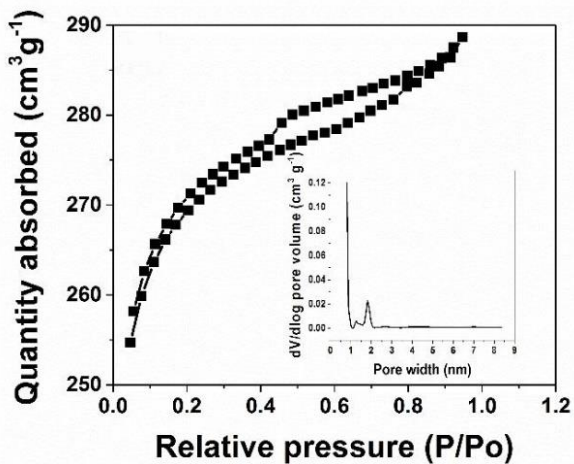


Figure 3: N₂ adsorption/desorption analysis

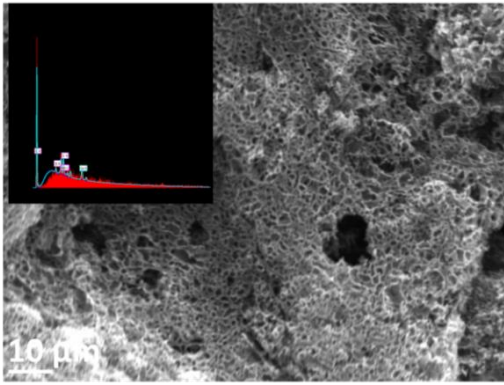


Figure 4: SEM analysis of the samples with inset of EDS

The ash content, moisture content, volatile matter and fixed carbon contents of the cassava peels was ascertained by carrying out proximate analysis using the ASTM methods (Kumar and Jena, 2016). The fixed carbon content of the sample was calculated by mass difference. The proximate composition of the material is as presented in Table 1. The suitability of cassava peel as precursor for activated carbon was confirmed by these results which showed that the fixed carbon content in the raw material is 80.53wt %.

XRD analysis was carried out to confirm the phase composition of the material. As can be seen from Figure 1, the XRD patterns for the prepared AC sample showed an amorphous signature (i.e. broad diffraction peaks) at a 2-theta angle of 24–25° and 42–44° corresponding to the (002) and (100) crystallographic planes of a carbon material [15]. The degree of graphitization of the carbon material was confirmed by using Raman spectroscopy as shown in Figure 2. The Raman shift as displayed shows the conspicuous peaks representing the G (graphitic) and D (diamond) phases of carbon with values of 1595cm⁻¹ and 1359cm⁻¹ respectively. The higher peak which shows the graphitic phase, shows that the material is highly graphitized. The morphology of the cassava peel derived activated carbon was determined by the scanning electron microscope (SEM) analysis and as displayed in Figure 4, it can be seen that the activated

carbon consists of both micropores and mesopores. The inset of SEM micrograph is the elemental dispersive spectra (EDS) which display the elemental composition of the material as further seen in Table 2 with carbon content showing the highest peak, as the most present composite.

A Nitrogen adsorption/desorption analyser was used to get a better understanding of the pore structure of the carbon material. In Figure 3, the adsorption isotherms from the beginning corresponds to micropore adsorption [16]. It can be noticed that a type IV hysteresis loop is formed later on showing the presence of mesopores. The sample shows adsorption-desorption sharp curve at a relatively low pressure while a hysteresis loop is observed at P/P₀ > 0.45, which indicates the coexistence of mesoporous and microporous structures [17]. The KOH activated carbon showed a well-developed porous architecture having a BET surface area of 828 m²g⁻¹ (Table 3), the total mesopore and micropore volume otherwise known as the total pore volume was estimated to be 0.3981m³g⁻¹ and having a pore diameter of 2.66nm.

In Table 4, a comparison is made with other precursors and even cassava peels on the achieved surface area as reported by various researchers. The results achieved from this research clearly outperforms the others in terms of specific surface area.

Table 4: Comparison of Specific surface area of different materials

Materials	Activating agent	Specific surface Area (m ² g ⁻¹)	Ref
Waste tires	H ₃ PO ₄	563	[18]
Petals	Physical (CO ₂)	509	[19]
Rubber seed shell	KOH	620	[20]
Cassava peel	FeCl ₃	405.9	[21]
Cassava peel	KOH	828	This

work

CONCLUSION

The results achieved clearly show that cassava peel derived activated carbon can be used for multiple purposes. KOH activation also proves better than FeCl₃ as it delivers greater surface area and allows for better pore volume for application as a good adsorption material. Its porosity and high surface area can also be explored for energy storage applications.

REFERENCES

- [1] Nwabanne, Igbokwe P K, Preparation of Activated Carbon from Nipa Palm Nut: Influence of Preparation Conditions, 2011. www.isca.in.
- [2] M. Sevilla, A.B. Fuertes, Direct synthesis of highly porous interconnected carbon nanosheets and their application as high-performance supercapacitors, *ACS Nano*. 8 (2014) 5069–5078. <https://doi.org/10.1021/nn501124h>.
- [3] L. Yao, G. Yang, P. Han, Z. Tang, J. Yang, Three-dimensional beehive-like hierarchical porous polyacrylonitrile-based carbons as a high performance supercapacitor electrodes Three-dimensional beehive-like hierarchical porous polyacrylonitrile-based carbons as a high performance supercapacitor elec, *J. Power Sources*. 315 (2016) 209–217. <https://doi.org/10.1016/j.jpowsour.2016.03.006>.
- [4] M. Sevilla, R. Mokaya, Energy storage applications of activated carbons supercapacitors and hydrogen storage - Energy & Environmental Science (RSC Publishing), (n.d.).
- [5] B. Moyo, D. Momodu, O. Fasakin, J. Dangbegnon, N. Manyala, Electrochemical analysis of nanoporous carbons derived from activation of polypyrrole for stable supercapacitors, *J. Mater. Sci.* (1911). <https://doi.org/10.1007/s10853-017-1911-y>.
- [6] A.E. Ismanto, S. Wang, F.E. Soetaredjo, S. Ismadji, Preparation of capacitor's electrode from cassava peel waste, *Bioresour. Technol.* 101 (2010) 3534–3540. <https://doi.org/10.1016/j.biortech.2009.12.123>.
- [7] X. Ma, H. Yang, L. Yu, Y. Chen, Y. Li, Preparation, surface and pore structure of high surface area activated carbon fibers from bamboo by steam activation, *Materials (Basel)*. 7 (2014) 4431–4441. <https://doi.org/10.3390/ma7064431>.
- [8] S.M. Yakout, G. Sharaf El-Deen, Characterization of activated carbon prepared by phosphoric acid activation of olive stones, *Arab. J. Chem.* 9 (2016) S1155–S1162. <https://doi.org/10.1016/j.arabjc.2011.12.002>.
- [9] S. Yang, K. Zhang, Converting Corn cob to Activated Porous Carbon for Supercapacitor Application, *Nanomaterials*. 8 (2018) 181. <https://doi.org/10.3390/nano8040181>.
- [10] Y. Huang, J. He, Y. Luan, Y. Jiang, S. Guo, X. Zhang, C. Tian, B. Jiang, Promising biomass-derived hierarchical porous carbon material for high performance supercapacitor, *RSC Adv.* 7 (2017) 10385–10390. <https://doi.org/10.1039/C6RA27788H>.
- [11] M. Sevilla, A.B. Fuertes, green approach supercapacitor electrodes : chemical activation of hydrochar with potassium bicarbonate, (n.d.) 1–31.
- [12] P. Ponkarthikeyan, K.S. Sree, A Review Of Activated Carbon By Chemical Activation, *SSRG Int. J. Civ. Eng.* (2017) 524–531. <http://www.internationaljournalsrsg.org/IJCE/2017/Special-Issue/ICRTCETM/IJCE-ICRTCETM-P197.pdf>.
- [13] S.M. Lamine, C. Ridha, H.M. Mahfoud, C. Mouad, B. Lotfi, A.H. Al-Dujaili, Chemical activation of an activated carbon prepared from coffee residue, *Energy Procedia*. 50 (2014) 393–400. <https://doi.org/10.1016/j.egypro.2014.06.047>.
- [14] A. Kumar, H.M. Jena, Preparation and characterization of high surface area activated carbon from Fox nut (*Euryale ferox*) shell by chemical activation with H₃PO₄, *Results Phys.* 6 (2016) 651–658. <https://doi.org/10.1016/j.rinp.2016.09.012>.
- [15] F. Barzegar, A.A. Khaleed, F.U. Ugbo, K.O. Oyeniran, D.Y. Momodu, A. Bello, J.K. Dangbegnon, N. Manyala, Cycling and floating performance of symmetric supercapacitor derived from coconut shell biomass, *AIP Adv.* 6 (2016). <https://doi.org/10.1063/1.4967348>.
- [16] X.B. Xie, D. Wu, H. Wu, C. Hou, X. Sun, Y. Zhang, R. Yu, S. Zhang, B. Wang, W. Du, Dielectric parameters of activated carbon derived from rosewood and corncob, *J. Mater. Sci. Mater. Electron.* 31 (2020) 18077–18084. <https://doi.org/10.1007/s10854-020-04358-8>.
- [17] T.E. Amakoromo, O.E. Abumere, J.A. Amusan, V. Anye, A. Bello, Porous Carbon from Manihot Esculenta (Cassava) Peels Waste for Charge Storage Applications, *Curr. Res. Green Sustain. Chem.* 4 (2021) 100098. <https://doi.org/10.1016/j.crgsc.2021.100098>.

-
- Tarila Ebibo Amakoromo is currently pursuing PhD degree program Department of Physics, University of Port Harcourt, Rivers state Nigeria PH+2348061645797 E-mail: tarila.amakoromo@uniport.edu.ng
 - Joseph Abiodun Amusan is currently a senior lecturer in the Department of Physics, University of Port Harcourt, PH+2348035622473, E-mail: joseph.amusan@uniport.edu.ng
 - Oamen Eronmonse Abumere is a Professor in the Department of Physics, University of Port Harcourt, PH+2348101700111, E-mail: oamen.abumere@uniport.edu.ng

- [18] N.W. Mingjia Zhi, Feng Yang, Fanke Meng, Minqi Li, Ayyakkannu Manivanna, Effects of Pore Structure on Performance of An Activated-Carbon Supercapacitor Electrode Recycled from Scrap Waste Tires. *ACS Sustainable Chemistry & Engineering*, 2(7), 1592–1598 | 10.1021/sc500336h, (2014). <https://sci-hub.se/10.1021/sc500336h> (accessed 17 January 2021).
- [19] X. Yu, Y. Wang, L. Li, H. Li, Y. Shang, Soft and wrinkled carbon membranes derived from petals for flexible supercapacitors *OPEN*, (2017). <https://doi.org/10.1038/srep45378>.
- [20] T. Pagketanang, A. Artnaseaw, P. Wongwicha, M. Thabuot, Microporous Activated Carbon from KOH-Activation of Rubber Seed-Shells Microporous Activated Carbon from KOH-Activation of Rubber Seed-Shells for Application in Capacitor Electrode, Elsevier B.V., 2015. <https://doi.org/10.1016/j.egypro.2015.11.550>.
- [21] G. Kounou Ndongo, N. Julius Nsami, K. Joseph Mbadcam, Ferromagnetic Activated Carbon from Cassava (*Manihot dulcis*) Peels Activated by Iron(III) Chloride: Synthesis and Characterization, n.d.