

Fiber Studies and Pulping Experiments on Empty Fruit Bunch (EFB) of Oil Palm (*Elaeis Guineensis*) Using Soda-AQ Process

Henry Okwudili CHIBUDIKE¹, Eze MGBACHIUZO¹, Nelly Acha NDUKWE², Nkemdilim Ifeanyi OBI³,
Olubamike Adetutu ADEYOJU⁴, and Eunice Chinedum CHIBUDIKE⁵

¹Chemical, Fiber and Environmental Technology Department, Federal Institute of Industrial Research, Oshodi, Lagos-Nigeria

²Department of Chemical Sciences, College of Basic & Applied Sciences, Mountain Top University, Magoki, Ogun State, Nigeria

³National Oil Spill Detection and Response Agency (NOSDRA), Abuja-Nigeria

⁴Production, Analytical and Laboratory Management, Federal Institute of Industrial Research, Oshodi, F.I.I.R.O., Lagos-Nigeria

⁵Planning, Technology Transfer and Information Management, Federal Institute of Industrial Research, Oshodi., Lagos-Nigeria

Abstract

Comparative assessment of physico-chemical characteristics, anatomic properties and economic relevance of Empty Fruit Bunch of Oil Palm (EFB) to the pulp and paper industry was investigated. Sample preparation was conducted in accordance with TAPPI Standard T12 – OS – 75, which specifies that samples be grinded to a fine particle size to permeate 0.4mm screen and retained on a 0.6mm screen. The Moisture content, Lignin, Extractives, Alpha cellulose, Ash content and fiber dimensions were investigated. The pulping investigation had four (4) factors at three (3) different levels each: Factor 1, cooking temperature (150, 160 and 170°C) ; Factor 2, cooking time (60, 90 and 120minutes); Factor 3, liquor concentration (10%, 15% and 20% NaOH charge); and Factor 4, anthraquinone concentration (0.00%, 0.25% and 0.50%). The experimental design had 3×3×3×3 i.e., 81 pulping scenarios. Pulping Operation was subsequently carried out by the Soda-AQ Process which resulted in the production of pulp and paper samples. Pulp Yields was in the range of 29.56 to 49.97% calculated on oven dry (O.D) basis. The resultant pulps obtained from the cooking operation had very good feel, and exhibited fairly bright color, with slightly slow tendency to felt, thereby making drainage and consequent paper making time short. Over-all parameter achieved asserts that oil palm fronds (woody petioles) have a promising future (when used in blend with long fiber pulp) in substituting wood in the pulp, paper and fiber- board industry.

Keywords: Empty Fruit Bunch of Oil Palm (EFB), kappa number, Lignin, Oven dried, Pulp screened yield, Soda-AQ, Tappi standards

1. INTRODUCTION

As the importance of paper extends from the home as toiletries, government and schools/academic institutions as writing and printing materials, and in the industries as wrapping/packing materials, it becomes necessary to study by research to discover ways of converting waste materials to pulp and paper in order to meet the growing requirement as well as reduce the cost of paper materials in Nigeria, hence, the extensive physico-chemical analysis on oil palm wastes (Chibudike, 2011).

The Oil Palm is a major source of vegetable oil, ranking next to coconut in importance. Palm Oil become known to the western world when Portuguese explorers sailed south and eastward around the hump of Africa. According to the Commonwealth Economic Committee (1956), a total of 845,000 m. tons of palm kernels and 664,000 m. tons of oil was produced in the world in 1955, with West Africa supplying the bulk. About 50% of the kernels, 421,000 m. tons, came from Nigeria alone. The chemical constituents of Oil palm wastes are carbon, oxygen, hydrogen, ash (largely silica). They are composed of cellulose; other carbohydrates present are starch, sugar, and lignin, which act as an adhesive for cellulose (FAO, 2009)

Oil palm trees are chiefly grown in the Southern part of Nigeria, and other parts of West Africa. Where oil palms are majorly processed, palm bunches and palm fronds constitute wastes (bye products). These residues are woody petioles (leaf stems) often used for fencing, the trunks of the trees for building, and the high quality animal folder are used by local craftsmen who plait the leaves into thatch and the fronds into brooms and baskets. The discarded bunches of the oil palm are used as substitute for firewood while the sap of the tree serves as good source of palm wine. The residue from the oil-extraction process constitutes useful domestic needs and also provide valuable source of income for many small holders in a variety of ways (F.A.O., 2009). However, the percentage of these residue usefully utilized are quite low, the rest constitute waste and nuisance to the environment which end up being burned for no beneficial

purpose. Most often, these waste materials pose disposal problem which constitute nuisance to the environments where they are processed. They often have negative value as resources are employed to burn the materials on site or transport for disposal elsewhere. The common method of disposal by burning causes a great deal of pollution and is a menace to the environment (Chibudike, 2019).

Paper is defined as “thin sheets of compressed vegetable cellulose fibre”. It is used for writing and printing, for wrapping and packing and for many other varieties of special purpose, from filtering precipitates from solution and to make building material. In modern society, paper is a basic material. The development of well-developed machineries to produce it has been largely responsible for increasing literacy, and raising educational levels throughout the world. Wood is composed of cellulose; other carbohydrates present are starch, sugar and lignin, which act as an adhesive for cellulose (some other adhesive used are gum, mucilage, lattice and resins. Paper sources are primarily from wood, which is composed of cellulose fibres that exist as small tubes oriented along the length of the trees. In plants fibres, woody cells formed at the active area of growth between the bark of the wood constitute the cambial layer. The fibres help in water transportation. These fibres are the most important part of the tree used in papermaking. At some time in the process of industrialization, urban requirements for wood would begin to put heavy and increasing demands on the forest. The use of non-wood fibrous plants for the production of pulp and paper should be the attainment of the highest economic use of these materials. It is believed that waste utilization can assist in reviving Nigerian Economy (Steward, 2001 and 2003).

2. EXPERIMENTAL

2.1 Materials

The Empty Fruit Bunch of Oil Palm (EFB) used in this experimental work was obtained during post-harvest treatment in Oke Ira, Ebute-Metta (West) Local Government Area of Lagos State, Nigeria.

2.2 Raw Material Characterization

Prior to chemical characterization and pulping, the raw material was washed, cleaned, sorted to remove foreign matters and air-dried, then stored to less than 60% relative humidity and aerated from time to time, to avoid decay. Following drying at ambient temperature, the raw material was cold-ground in a Wiley mill, to avoid altering its composition, permeating 0.25mm and retained on a 0.40mm sieve to keep size fractions between 0.25 and 0.40 mm using No. 25 and 40 of the Tyler series in accordance with TAPPI Standard T12-oS-75. Particles larger than 0.40 mm are inefficiently attacked by the chemical reagents, whereas those below 0.25 mm can cause filtering problems. The sample was characterized by analyzing its content of moisture, hot water solubility, klason lignin, α -cellulose, 1% NaOH solubility, total extractives and ash. Standard procedures were used for the analyses of these parameters and these procedures are outlined in Table 1.

2.3 Determination of Fiber Morphology

Small slivers were obtained and macerated with 10 ml of 67% HNO₃ and boiled in a water bath ($100 \pm 2^{\circ}\text{C}$) for 10 min (Ogbonnaya et al., 1997). The slivers were then washed, placed in small flasks with 50 ml distilled water and the fiber bundles were separated into individual fibers using a small mixer with a plastic end to avoid fiber breaking. The macerated fibers suspension were finally placed on a slide (standard, 7.5 cm \times 2.5 cm) by means of a medicine dropper and stained with 1:1 aniline sulfate–glycerin mixture to enhance cell-wall visibility (cell walls retain a characteristic yellowish color) and easier measurement. About twenty (20) fibers were measured per each sample at a magnification of X 101 on a Reichort visopam projection microscope and fiber diameter, lumen diameter, cell wall thickness and cross-sections were obtained. All samples were measured in a swollen condition.

2.4 Outline of the Production Process

Figure 1 illustrates the process of making paper from Empty Fruit Bunch of Oil Palm (EFB). The sample was characterized chemically and morphologically and converted into brown pulp at a delignification degree of 18.2 kappa from Soda-AQ Process. The resulting pulps was fully bleached by the D1-Ep-D2 sequence and characterized for its beatability, drainability and physical-mechanical properties.

2.5 Description of the Pulp and Paper-making Process

The sample was shredded prior to chemical characterization and pulping, a portion of the shredded sample was washed, cleaned, sorted to remove foreign matters and air-dried, then stored to less than 60% relative humidity and aerated from time to time, to avoid decay. Following drying at ambient temperature, the raw material was cold-ground in a Wiley mill, to avoid altering its composition, permeating 0.25mm (because samples below 0.25 mm can cause filtering problems) and retained on a 0.40mm sieve (because particles larger than 0.40 mm are inefficiently attacked by the chemical reagents) to keep size fractions between 0.25 and 0.40

mm using No. 25 and 40 of the Tyler series in accordance with TAPPI Standard T12 – oS – 75. This portion of the sample was characterized by analyzing its content of moisture, hot water solubility, klason lignin, α -cellulose, total extractives and ash. Standard procedures were used for the analyses of these parameters and these procedures are outlined in table 1. The second portion of the shredded sample was subjected to a thorough cleaning process, 2kg of air-dry sample was loaded into a 15 L capacity batch reactor (digester) with eight (8) liter cooking liquor at liquor-sample ratio of 4:1. The digester is furnished with an outer electrical heating jacket. The lid of the digester was firmly bolted to prevent leakage, the digester was switched on and the time of rise of temperature and pressure was noted at intervals of five (5) minutes. The content of the digester was stirred while in operation by rotating the vessel via a motor connected through a rotary axle to a control unit, including measurement and control instruments of pressure and temperature, to facilitate attainment of the working temperature (5°C/min). The pulping temperatures gradually rose to the maximum cooking temperature of 150oC within a period of 61 minutes and allowed to be steady at this temperature for minimum of 29 minutes. The digester was switched off after maximum cooking period of 90 minutes from start of operation and allowed to cool below 60oC before the content were blown down. The digester’s initial temperature, pressure and starting time were all noted, and the various changes in these parameters were also recorded. The resultant pulp was subjected to thorough washing with plenty of water. When it was observed that subsequent washing resulted in no further change in color, the pulp was transferred into the valley beater for processing into a more refined pulp before the bleaching operation.

Table 1 Standards used in the Chemical Characterization

Agro-biomass Characterization	Standards
Sample preparation	TAPPI Standard Test Method T 12 oS-75
Moisture	TAPPI Standard Test Method T 264 om-88
Hot water solubility	TAPPI Standard Test Method T 207 cm-99
Total Extractives	TAPPI Standard Test Method T 204 cm-97
Acid insoluble (klason) lignin	TAPPI Standard Test Method T 222 om-02
Alpha (α)-cellulose	TAPPI Standard Test Method T 203 os-74
1% NaOH solubility	TAPPI Standard Test Method T4 os-59
Ash	TAPPI Standard Test Method 211 om -02
Holocellulose	TAPPI standard Test method T-249, 2004
Kappa No.	TAPPI Standard Test Method T236 om-06
Viscosity	TAPPI Standard Test Method T230 om-08
Brightness	TAPPI Standard Test Method T452 om-08

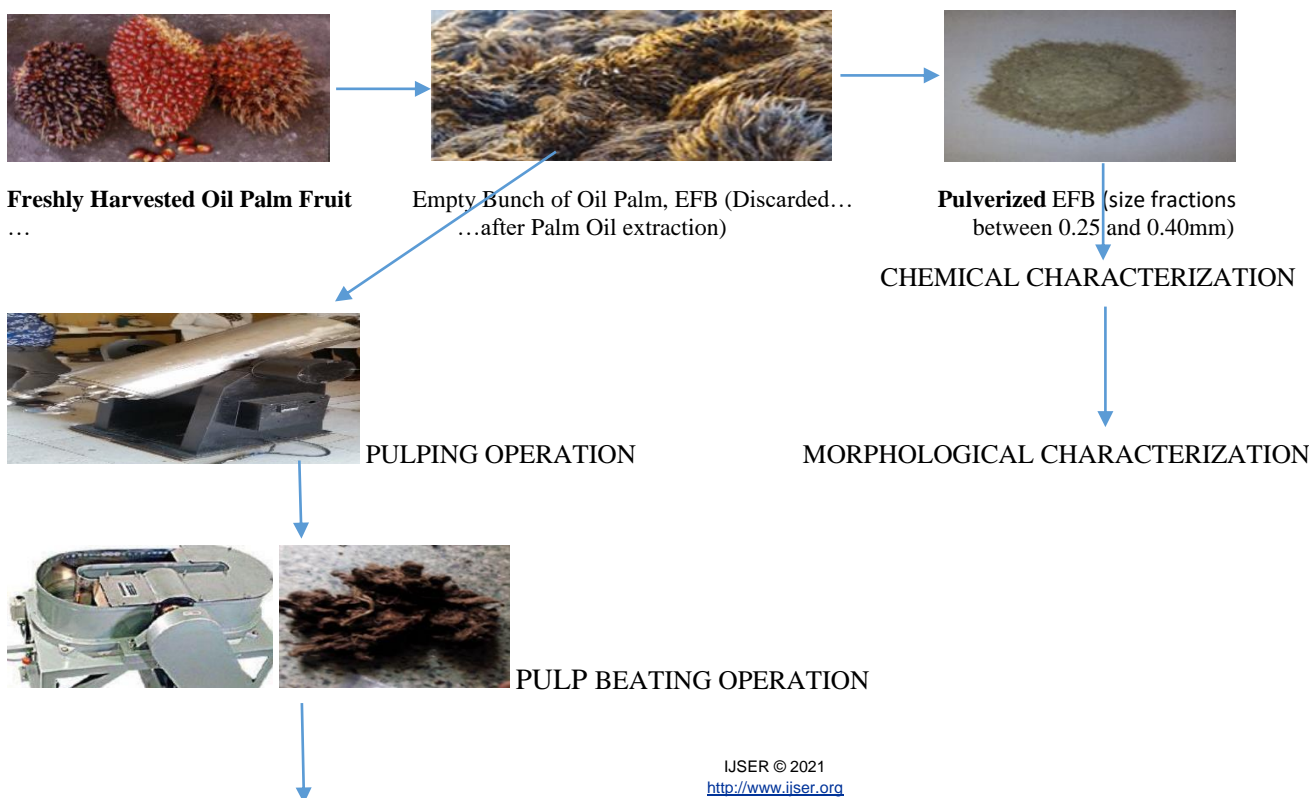




Figure 1: Steps in Oil Palm EFB (Agro-biomass) fractionation and conversion to paper

Table 2: Pulping Conditions for Empty Fruit Bunch of Oil Palm (EFB) Investigated

Conditions of Pulping Operation	Parameters
Air dry weight of EFB (kg) (A.D)	2
Liquor charge (%)	10, 15 and 20
pH of white liquor	6
pH of black/spent liquor	3
Liquor/biomass ratio	4:1
Maximum cooking temperature (°C)	150, 160 and 170
Time to reach maximum temperature (minutes)	40
Time at maximum temperature (minutes)	20, 50 and 80
Over-all cooking time (minutes)	60, 90, 120
Blow-down temperature (°C)	60

3. RESULTS AND DISCUSSION

3.1 Chemical Properties of Empty Fruit Bunch of Oil Palm (EFB)

Chemical analyses of EFB was conducted. Table 3 illustrates the results of the characteristics obtained. The moisture content and hot water solubility of EFB is quite low, while the extractive content is also low compared to other agricultural residues studied in previous investigation, which means that Oil Palm EFB contain less substances like waxes, fats, resins, phytosterols, non-volatile hydrocarbons, low molecular weight carbohydrates, salts and other water-soluble substances.

A higher content of extractives would be converted into pitch, which would adversely affect the runnability of process equipment and the quality of furnished paper because of shadow marking. Empty Fruit Bunch of Oil Palm has slightly high content of extractives hence would require a moderately high dose of pulping liquor to neutralize acidic extractive, which would have little or no effect on the pulp yield and might create less digester corrosion caused by extractives. The higher the lignin content, the greater the stiffness of fibers. Lignin contents in Empty fruit Bunch of Oil Palm is quite low and almost similar with that of the softwood. As observed in Table 3, Klason lignin contents in Empty Fruit Bunch of Oil Palm (EFB) is (16.09%). In practice, this means that these materials would need milder pulping conditions (lower temperatures and chemical charges) in order to reach a satisfactory kappa number and it would also undergo bleaching more easily and with the utilization of fewer chemicals. The average fiber dimensions of Empty Fruit Bunch of Oil Palm investigated in this research study is shown in Tables 4. Despite the decrease in the value of lignin, the extractive content, and ash in addition to decrease in chemical consumption and cooking time, pulp yield was expectedly high. Papers made from this type of fiber might show reduced water absorbency.

3.2 Analyses of the Morphological Properties of Empty Fruit Bunch of Oil Palm (EFB)

The morphological parameters of Empty Fruit Bunch of Oil Palm investigated are presented in table 4. The Fiber length of EFB is 0.9610, the Fiber diameter is 14.16µm, fiber lumen width is 5.97µm while the Fiber cell wall thickness is 4.04µm. Softwood fiber is between 3-5 mm long and about 39 to 41 µm wide, meaning that EFB fiber length and width are about 66% to 80% and 62.56% to 65.46 lower, respectively, than those of softwood.

Table 3: Chemical Characterization of Empty Fruit Bunch of Oil Palm (EFB)

Parameters	Empty Fruit Bunch of Oil Palm (EFB)
Source of Sample (Geographical Location)	Southern Nigeria
Age of Maturity (years)	6-8
Moisture content (%)	12.25
Hot Water Solubility (%) @ 80-95°C for 0.5hr	9.65

Extractives (%)	13.9
Ash (%)	4.55
Alpha-cellulose (%)	45.57
Lignin (%)	16.09
Holocellulose (%)	69.80
Pulp yield (%)	49.97

Table 4 Morphological properties of Empty Fruit Bunch of Oil Palm (EFB)

Plant Materials	Fibre length, (L), (mm)	Fibre diameter, (D), (µm)	Fibre Lumen, (d), diameter (µm)	Fibre wall/Cell wall thickness, (w), (µm)
Empty Fruit Bunch Oil Palm	0.9610	14.16	5.97	4.04

Table 5: Biometry/Morphological Indices of Fiber Dimensions

Plant materials	Derived Values			
	Slenderness ratio, L/D	Flexibility coefficient, (d/D)×100	Runkel ratio, 2w/d	Rigidity Coefficient, 2w/D
EFB	67.8672	42.16	1.35	0.57

Table 6. Design Layout of Independent Variables (Factors) and the Dependent Variables (Responses) for the Pulping Process

Experimental Run	Factor 1	Factor 2	Factor 3	Factor 4	Response 1
	A:Anthraquinone (% o.d. biomass)	B: Soda Charge (%)	C:Temperature (°C)	D: Cooking Time (Minutes)	Pulp Screened Yield %
1	0.00	10	150	60	40.19
2	0.25	10	150	60	40.25
3	0.50	10	150	60	40.77
4	0.00	15	150	60	42.94
5	0.25	15	150	60	42.99
6	0.50	15	150	60	41.76
7	0.00	20	150	60	41.54
8	0.25	20	150	60	40.47
9	0.50	20	150	60	42.43
10	0.00	10	160	60	40.91
11	0.25	10	160	60	41.61
12	0.50	10	160	60	41.22
13	0.00	15	160	60	39.11
14	0.25	15	160	60	41.23
15	0.50	15	160	60	42.01
16	0.00	20	160	60	41.30
17	0.25	20	160	60	41.14
18	0.50	20	160	60	41.97
19	0.00	10	170	60	39.31
20	0.25	10	170	60	38.03
21	0.50	10	170	60	40.01
22	0.00	15	170	60	37.00
23	0.25	15	170	60	41.07
24	0.50	15	170	60	41.11
25	0.00	20	170	60	39.55
26	0.25	20	170	60	38.43
27	0.50	20	170	60	39.01
28	0.00	10	150	90	41.99
29	0.25	10	150	90	43.22
30	0.50	10	150	90	44.99
31	0.00	15	150	90	41.44
32	0.25	15	150	90	49.97

33	0.50	15	150	90	47.81
34	0.00	20	150	90	45.11
35	0.25	20	150	90	46.41
36	0.50	20	150	90	47.66
37	0.00	10	160	90	45.54
38	0.25	10	160	90	44.33
39	0.50	10	160	90	43.32
40	0.00	15	160	90	42.04
41	0.25	15	160	90	46.54
42	0.50	15	160	90	45.67
43	0.00	20	160	90	40.30
44	0.25	20	160	90	44.88
45	0.50	20	160	90	45.55
46	0.00	10	170	90	38.53
47	0.25	10	170	90	40.56
48	0.50	10	170	90	41.09
49	0.00	15	170	90	35.98
50	0.25	15	170	90	41.00
51	0.50	15	170	90	42.98
52	0.00	20	170	90	39.88
53	0.25	20	170	90	44.65
54	0.50	20	170	90	40.64
55	0.00	10	150	120	43.78
56	0.25	10	150	120	37.11
57	0.50	10	150	120	36.00
58	0.00	15	150	120	41.04
59	0.25	15	150	120	44.79
60	0.50	15	150	120	43.76
61	0.00	20	150	120	36.34
62	0.25	20	150	120	41.99
63	0.50	20	150	120	40.76
64	0.00	10	160	120	34.77
65	0.25	10	160	120	38.79
66	0.50	10	160	120	35.34
67	0.00	15	160	120	39.44
68	0.25	15	160	120	41.55
69	0.50	15	160	120	40.51
70	0.00	20	160	120	35.31
71	0.25	20	160	120	34.33
72	0.50	20	160	120	33.99
73	0.00	10	170	120	32.76
74	0.25	10	170	120	35.45
75	0.50	10	170	120	35.56
76	0.00	15	170	120	32.99
77	0.25	15	170	120	31.09
78	0.50	15	170	120	42.46
79	0.00	20	170	120	40.66
80	0.25	20	170	120	39.43
81	0.50	20	170	120	37.77



Figure 2: Fiber image of Oil Palm EFB on projection microscope

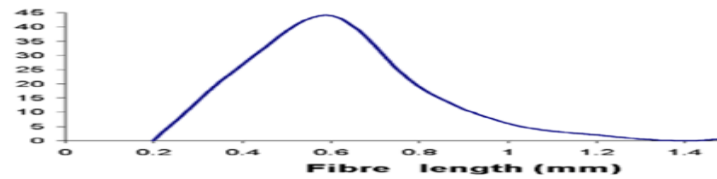


Figure 3: Distribution of EFB Fiber Length

3.3 Design Matrix Evaluation for Response Surface Quadratic Model

4 Factors: A(cooking temp.), B(cooking time), C(liquor concentration), and D(anthraquinone concentration). No aliases were found for Quadratic Model.

Table 7. Degrees of Freedom for Evaluation

Model	14
Lack Of Fit	14
Corr Total	29
Residuals	15
Pure Error	1

Table 8. Sequential Model Sum of Squares

Source	Sum of Squares	DF	Mean Square	F Value	Prob > F	
Mean	58534.08	1	58534.08			<u>Suggested</u>
Linear	21.94	4	5.49	1.31	0.2932	
2FI	16.84	6	2.81	0.61	0.7213	
<u>Quadratic</u>	<u>45.78</u>	<u>4</u>	<u>11.45</u>	<u>4.09</u>	<u>0.0195</u>	<u>Suggested</u>
Cubic	35.41	13	2.72	0.83	0.6702	Aliased
Residual	29.81	2	3.29			
Total	58660.65	30	1955.35			

Table 9. Lack of Fit Tests

Source	Sum of Squares	DF	Mean Square	F Value	Prob > F	
Linear	98.03	24	4.08	0.62	0.7837	
2FI	81.19	18	4.51	0.68	0.7575	
<u>Quadratic</u>	<u>35.41</u>	<u>14</u>	<u>2.53</u>	<u>0.38</u>	<u>0.8712</u>	<u>Suggested</u>
Cubic	6.545E-004	1	6.545E-004	9.935E-005	0.9937	Aliased
Pure Error	6.59	1	6.59			

"Lack of Fit Tests": Want the selected model to have insignificant lack-of-fit.

Table 10. Model Summary Statistics

Source	Std. Dev.	R-Squared	Adjusted R-Squared	Predicted R-Squared	PRESS	
Linear	2.05	0.1734	0.0411	-0.1617	147.03	
2FI	2.15	0.3064	-0.0586	-1.2191	280.86	
<u>Quadratic</u>	<u>1.67</u>	<u>0.6682</u>	<u>0.3584</u>	<u>-0.3760</u>	<u>174.14</u>	<u>Suggested</u>
Cubic	1.82	0.9479	0.2451		+	Aliased

+ Case(s) with leverage of 1.0000: PRESS statistic not defined

Table 11. ANOVA for Response Surface Mean Model [Partial sum of squares]

Source	Sum of Squares	DF	Mean Square	F Value	Prob > F	
Model	84.56	14	6.04	2.16	0.0759	not significant

A	1.087E-004	1	1.087E-004	3.881E-005	0.9951	
B	0.72	1	0.72	0.26	0.6195	
C	2.81	1	2.81	1.00	0.3322	
D	2.026E-003	1	2.026E-003	7.237E-004	0.9789	
A ²	2.44	1	2.44	0.87	0.3658	
B ²	6.44	1	6.44	2.30	0.1501	
C ²	8.676E-003	1	8.676E-003	3.099E-003	0.9563	
D ²	34.28	1	34.28	12.24	0.0032	
AB	3.26	1	3.26	1.16	0.2978	
AC	2.16	1	2.16	0.77	0.3936	
AD	0.17	1	0.17	0.061	0.8078	
BC	1.71	1	1.71	0.61	0.4470	
BD	5.52	1	5.52	1.97	0.1808	
CD	0.86	1	0.86	0.31	0.5867	
Residual	42.00	15	2.80			
Lack of Fit	35.41	14	2.53	0.38	0.8712	not significant
Pure Error	6.59	1	6.59			
Cor Total	126.56	29				

Values of "Prob > F" less than 0.0500 indicate model terms are significant. In this case D² are significant model terms. Values greater than 0.1000 indicate the model terms are not significant. If there are many insignificant model terms (not counting those required to support hierarchy), model reduction may improve model.

The "Lack of Fit F-value" of 0.38 implies the Lack of Fit is not significant relative to the pure error. Non-significant lack of fit is good -- we want the model to fit.

Std. Dev.	1.67	R-Squared	0.6682
Mean	44.17	Adj R-Squared	0.3584
C.V.	3.79	Pred R-Squared	-0.3760
PRESS	174.14	Adeq Precision	6.263

A negative "Pred R-Squared" implies that the overall mean is a better predictor of the response than the current model. The ratio of 6.263 indicates an adequate clue that this model can be used to navigate the design space.

Final Equation in Terms of Coded Factors:

$$\begin{aligned}
 &\text{Pulp Screened Yield} = +46.08 \\
 &\quad -4.454E-003 * A \\
 &\quad +0.36 * B \\
 &\quad -0.74 * C \\
 &\quad +0.032 * D \\
 &\quad -0.71 * A^2 \\
 &\quad -1.07 * B^2 \\
 &\quad +0.075 * C^2 \\
 &\quad -2.88 * D^2 \\
 &\quad -0.73 * A * B \\
 &\quad +0.68 * A * C \\
 &\quad +0.22 * A * D \\
 &\quad -0.71 * B * C \\
 &\quad -1.54 * B * D \\
 &\quad -0.70 * C * D
 \end{aligned}$$

Final Equation in Terms of Actual Factors:

$$\begin{aligned}
 &\text{Pulp Screened Yield} = +46.08 \\
 &\quad -31.57028 * \text{Anthraquinone} \\
 &\quad +4.69994 * \text{Soda Charge} \\
 &\quad +0.040900 * \text{Temperature} \\
 &\quad +1.09800 * \text{Cooking Time}
 \end{aligned}$$

-11.30170	* Anthraquinone ²
-0.042775	* Soda Charge ²
+7.52829E-004	* Temperature ²
-3.20165E-003	* Cooking Time ²
-0.58527	* Anthraquinone * Soda Charge
+0.27078	* Anthraquinone * Temperature
+0.029531	* Anthraquinone * Cooking Time
-0.014216	* Soda Charge * Temperature
-0.010260	* Soda Charge * Cooking Time
-2.33830E-003	* Temperature * Cooking Time

The equation in terms of actual factors can be used to make predictions about the response for given levels of each factor. Here, the levels should be specified in the original units for each factor.

Table 12: Coefficient table for the quadratic model

	Intercept	A	B	C	D	AB	AC	AD	BC	BD	CD	A ²	B ²	C ²
Pulp Screened Yield	46.08	-4.454E-003	+0.36	-0.74	+0.032	-0.73	+0.68	+0.22	-0.71	-1.54	-0.70	-0.71	-1.07	8.676E-003
p-values		0.9951	0.6195	0.3322	0.9789	0.2978	0.3936	0.8078	0.4470	0.1808	0.5867	0.3658	0.1501	0.9563

Therefore, the second-order polynomial equation for the Soda-AQ pulping process is expressed as follow:

$$\text{Pulp Screened Yield} = 46.08 - 4.454E-003A + 0.36B - 0.74C + 0.032D - 0.73AB + 0.68AC + 0.22AD - 0.71BC - 1.54BD - 0.70CD - 0.71A^2 - 1.07B^2 + 8.676E-003C^2$$

According to the monomial coefficient value of regression model equation, X₁=A=-4.454E-003 (Anthraquinone charge), X₂=B= +0.36 (Soda Charge), X₃=C=-0.74 (Temperature), X₄=D=+0.032 (Cooking Time), and the order of priority among the main effect of impact factors is Soda Charge (B=X₂)>Cooking Time (D=X₄)>Cooking Temperature(C=X₃)>Anthraquinone Charge(A=X₁)

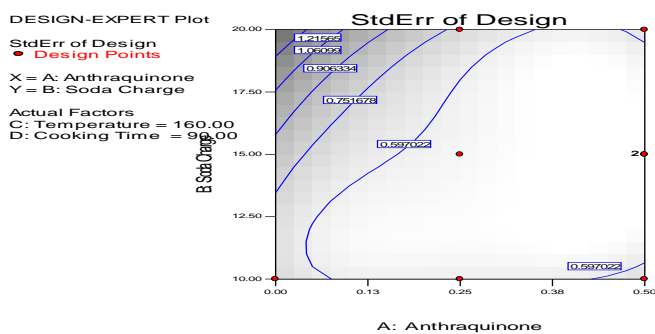


Figure 4: Standard Error of Design showing the effect of AQ

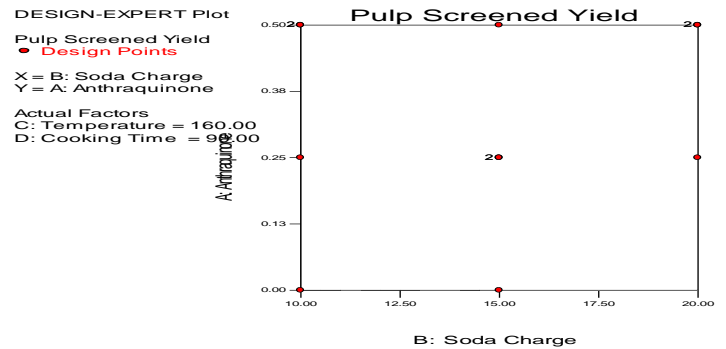


Figure 5: Model Graph of Pulp Screened Yield

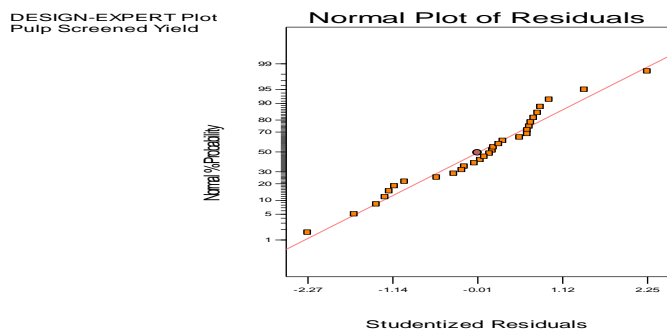


Figure 6: Normal Plot of Residuals

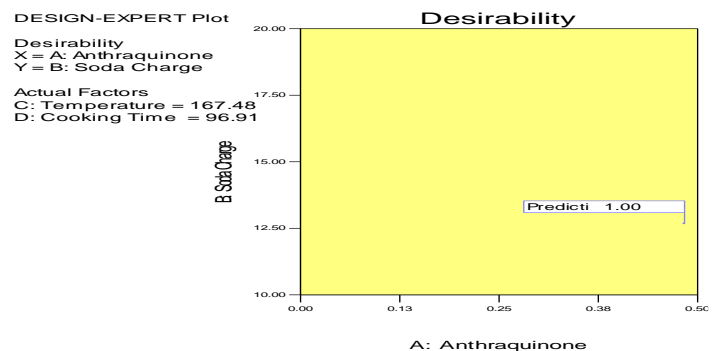


Figure 7: Desirability Plot of Numerical

Table 13. Optimization Solution Found for the Resonse Surface Mean Model (10 Solutions found. Number of Starting Points 10)

Solutions Number	Anthraquinone*	Soda Charge *	Temperature*	Cooking Time *	Desirability	Selected
1	<u>0.48</u>	<u>12.67</u>	<u>167.48</u>	<u>96.91</u>	<u>1.000</u>	<u>Selected</u>
2	0.48	10.06	167.82	112.18	1.000	
3	0.12	10.53	164.35	76.70	1.000	
4	0.49	10.81	161.53	117.07	1.000	
5	0.50	15.75	160.12	106.63	1.000	
6	0.06	11.21	152.67	73.83	1.000	
7	0.17	18.91	166.68	61.15	1.000	
8	0.28	17.42	151.08	74.27	1.000	
9	0.34	18.38	151.66	70.63	1.000	
10	0.42	11.89	151.09	86.95	1.000	

Influence of morphological properties on Biometry (Slenderness, Flexibility, Runkel and Rigidity coefficient) of the Oil Palm EFB fiber investigated are shown in Tables 5. The Slenderness ratio of Oil Palm EFB is 67.8672 while the Flexibility coefficient is 42.16. Generally, there are four different types of fibers which are classified under flexibility ratio (Bektas et al., 1990): (1) High elastic fibers having elasticity coefficient greater than 75; (2) Elastic fibers having elasticity ratio between 50 to 75; (3) Rigid fibers having elasticity ratio between 30 to 50; (4) High rigid fibers having elasticity ratio less than 30. According to this classification, flexibility coefficient of Oil Palm Woody Petiole is in uniformity with hardwoods. When Runkel proportion is greater than 1, it indicates that a fiber has thick wall and cellulose obtained from this type of fiber is less suitable for paper production; when it is equal to 1, it specifies that a cell wall has medium thickness and cellulose obtained from this type of fiber is suitable for paper production. When the rate is less than 1, it points out that a cell wall is thin and cellulose obtained from this fiber is the most suitable for production of paper (Eroglu et al., 1980; Xu et al., 2006). Runkel value of Oil Palm EFB (1.35) is greater than 1 and according to the Runkel classification, it specifies that the fiber has thick wall and cellulose obtained from this type of fiber is not very suitable for paper production except when used in blend with certain long fiber pulp plants like kenaf to boost its strength potential for producing certain types of paper materials. The low content of lignin in Oil Palm EFB (16.09%) made the fibers appear less tough and less stiffer compared to other fibers like pineapple leaves, wheat straws, corn stalk/sheets, coconut fruit bunch, elephant and lemon grass and other fibrous agro-wastes investigated in other studies furnishing rigidity coefficient following the order: (Highest) Bagasse (0.59)>Coconut (0.58)>EFB(0.57)> Pineapple leaves(0.56) > Corn(0.50)> Lemon grass (0.44)>kenaf(0.39) >Elephant grass (0.34) > Wheat(0.17)>Rice(0.06)>(lowest) (Chibudike et al., 2011). This is probably because lignin provides compressive strength to plant tissue and individual fibers and stiffens the cell walls, to protect carbohydrates from chemical and physical damages. Detailed research work on these agro-wastes is not included in this report.

At the end of the pulping operation, the pH of the cooking liquor dropped from 6.0 to 3.0 indicating that the anthraquinone performs certain functions besides that of Sodium Hydroxide increasing the hydroxide content of the liquor, thereby increasing the rate of lignin removal. The black liquor obtained after the digestion process was not discarded, but rather employed in further chemical analysis. The black liquor was distinctly alkaline, but not caustic owing to the fact that a large part of the alkali was present in the form of neutral compounds, hence the need for chemical recovery.

The Acid-insoluble lignin in the Oil Palm EFB was determined to be 16.09%. This necessitated the use of a mild liquor ranging from 10 to 20% for the cooking operation. Ash content of the Oil Palm EFB recorded 3.1% which is a measure of inorganic mineral present in the sample. These values afford more effective reuse of spent chemical after the pulping operation. The fibre length of the Oil Palm EFB recorded 0.9610mm which does not process the tendency to contribute to tensile strength of its corresponding furnished paper samples. This is the more reason why it is necessary to use EFB in blend with long fiber pulp plant in order to achieve better result. Alpha cellulose recorded a value of 45.57% which indicates the amount of un-degraded higher molecular weight cellulose present. The pulp yield is expectedly high (49.97%). This exert a very good beneficial effect. Temperature coefficient of delignification was determined to be approximately 2.0, indicating that an increase in cooking temperature by 5% might result in an increase in the rate of lignin removal.

All analytical tests were carried out in duplicate. Statistical analysis was performed using the Design Expert software. Data were analyzed by the analysis of variance (ANOVA), and p-value lower than 0.05 was considered significant in surface response analysis. The optimal values of the operation parameters were estimated by the three-dimensional response surface analysis of the independent variables (Cooking time, Liquor charge and Liquor/Biomass Ratio respectively) and the dependent variable (Pulp Yield =Y%). A negative "Pred R-Squared" implies that the overall mean is a better predictor of the response than the current model. The residuals are represented graphically by means of a residual plot as shown in figure 6. This normal probability plot indicates whether the residuals follow a normal distribution, thus follow the straight line. Here, the scatter had a definite pattern along the straight line which indicates that a transformation of the response may provide a better analysis.

Hence, the optimum pulping condition according to the selected optimization solution found is summarized as 96.91 minutes cooking time, 12.67% soda-charge, 167.48 °C cooking temperature and 0.48% anthraquinone charge, oven dried weight of biomass.

4. CONCLUSION AND RECOMMENDATION

Pulping is a chemical-technological process for the production of cellulose fibers for paper-making from woods and other plant materials. Paper strength depends on the cellulose content of a raw plant material. Cellulose content was at a satisfactory level (above 40%) for the fiber utilized in the present study. Overall, Empty Fruit Bunch of Oil Palm (EFB) appear to be suitable for producing paper products due to lower lignin and extractive components as well as higher in cellulose content, though short in fiber length. Literature studies about softwoods revealed that elasticity coefficient was found within the range 50-70. Examining this information given, and comparing it with data generated in this research study, it seems Oil Palm EFB is similar to other softwood fibers. Depending on all the investigation carried out, it is possible to conclude that Oil Palm EFB when used in blend with long fiber pulp plants would be suitable for good brightness paper production. Considering the summary of analyses of data generated in this research work in comparison with literature and previous studies on other agro-base fiber residues, Oil Palm EFB when used in blend with other long fibrous pulp plants like kenaf can be very suitable to furnish good paper based materials like fiber plate, rigid cardboard, cardboard, tissue, corrugating medium, printing and writing paper.

Agricultural wastes, annual plants and non-wood materials have attained such importance in the world cellulose economy, that to ignore their relevance in the pulp and paper industry would result in a complete lack of balance. In a world where virgin pulp sources are scarce, and environmental concerns require reduction in cutting down green forest, agricultural residues could become a good source of fiber in the tropical regions of the world where they are grown. The search for local long fiber pulp material which can be easily propagated remains one of the most important key desideratum for the eventual resuscitation of the present mom bund paper industries of Nigeria. One important way of stemming the tide of imports is to find a good substitute to fine pulp for the use of the Nigeria paper companies when they eventually start producing. Besides being an innovation and new entry into the pulp map, Oil Palm EFB can become the best gift of FIIRO into the future pulp market of the tropical world.

REFERENCES

Anonymous, 2002. Technical Association of the Pulp and Paper Industry: Sampling and Preparing Wood for analysis (TAPPI Standard Test Method T222 om-02), Atlanta, USA.

Anonymous, 2002. Technical Association of the Pulp and Paper Industry: Ash in wood, pulp, paper and paperboard: combustion at 525°C (TAPPI Standard Test Method T211 om-02), Atlanta, USA.

Anonymous, 2002. Technical Association of the Pulp and Paper Industry: One percent sodium hydroxide solubility of wood and pulp (TAPPI Standard Test Method T212 om-02), Atlanta, USA.

Anonymous, 1999. Technical Association of the Pulp and Paper Industry: Water solubility of wood and pulp (TAPPI Standard Test Method T207 cm-99), Atlanta, USA.

Anonymous, 2007. Technical Association of the Pulp and Paper Industry: Solvent extractives of wood and pulp (TAPPI Standard Test Method T204 cm-97), Atlanta, USA.

Anonymous, 1999. Technical Association of the Pulp and Paper Industry: Alpha-, beta- and gamma-cellulose in pulp (TAPPI Standard Test Method T203 cm-99), Atlanta, USA.

Anonymous, 2002. Technical Association of the Pulp and Paper Industry: Determination of Acid-insoluble lignin in wood and pulp (TAPPI Standard Test Method T210), Atlanta, USA.

Anonymous, 2004. Technical Association of the Pulp and Paper Industry: Determination of Holocellulose in wood and pulp (TAPPI Standard Test Method T210), Atlanta, USA.

Bektas, I., Tutus, A. and Eroglu, H. (1990) "A Study of the Suitability of Calabian Pine (*Pinus Brutia* Ten.) for Pulp and Paper Manufacture. Turkish J. Agric. For., 23: 589-597.

Casey J.P., (1980) Pulp and Paper: chemistry and chemical technology

Chibudike H.O., "Catalytic Enhancement of Monoethanolamine Pulping Process", PhD Thesis, International University, Bamenda (IUB), Cameroon, 2019 p. 72-92.

Chibudike H.O., Mgbachiuzo E., Adeyoju O.A., Kayode O.F., Arowolo A.B., Orekoya E.O., Tojola O.B. and Ojo B.I. (2011) "Studies of Fiber Characteristics and Paper -making Potentials of Agricultural Wastes", Nigerian Journal of Engineering Management (NJEM) , Vol. 12, No.1, pp 8 -11.

Eroglu H., Andreolety, Silvy J., and Cheradame H., (1980), "The Influence of Poly(styrene sulfonate) addition to Cellulosic Fibers by wet Processing on the Physico- mechanical Properties of Paper", Journal of Applied Polymer Science, Volume 25, Issue 5.

FAO. 2009. Food Security and Agricultural Mitigation in Developing Countries: Options for Capturing Synergies. Rome, Italy.

Ogbonnaya C.I., Roy-Macauley H., Nwalozie M.C., and Annerose D.J.M., (1997), "Physical and histochemical properties of kenaf (*Hibiscus cannabinus* L.) grown under water deficit on a sandy soil" Industrial Crops and Products 7(1): 9-18

Steward C. M. (2001): "The Selection and Preparation of a Reproducible Wood Sample for Chemical Studies", Australian Pulp and Paper Ind. Tech. Assoc. Proc. 5: 65-110, 112-114.

Steward C.M. (2003), "The Selection and Preparation of a Reproducible Wood Sample for Chemical Studies", Australian Pulp and Paper Ind. Tech. Assoc. Proc., 13, 16-32, 12-41.