

## Investigation of Morphological, Mechanical and Thermal Properties of Hot-Pressed Electrospun CNTs/Carbon nanofibril Composites by Positron Annihilation Technique

M. A. Elmeniawi<sup>a\*</sup>, K. R. Mahmoud<sup>b</sup> and Ashraf A. Ali<sup>c</sup>

<sup>a</sup>Materials Engineering Department, Faculty of Engineering, Zagazig University, Egypt, P.O. Box 44519

<sup>b</sup>Physics Department, Faculty of Science, Kafrelsheikh University, 33516 El Geesh Street, Kafr El Sheikh, Egypt

<sup>c</sup>Mechanical Design and Production Engineering Department, Faculty of Engineering, Zagazig University, Egypt, P.O. Box 44519

### Abstract

Three groups of Carbon nano tubes (CNTs) of three different diameters, and each with five different weight concentrations were dispersed in a polyacrylonitrile (PAN)/dimethylformamide (DMF) polymer solution. PAN/DMF with CNTs dispersions were electrospun under optimum electrospinning conditions, and the collected fabrics were thermally stabilized and carbonized under static pressure to activate the high surface energy aiming to build firm and strong fabrics. The resultant carbonized sixteen fabrics showed reddish color with strong (as maximum as 60MPa strength) and flexible (as maximum as 5% strain) behaviors. Morphological characterization by using SEM showed minimum average fibril diameter of  $130\pm 20$  nm for the smallest CNTs diameter. The effect of CNTs size on the electrospun fiber diameter has been investigated. Also, evaluation of the presence of CNTs inside the carbon nano fiber has been investigated by using HRTEM. Mechanical properties (strength and modulus of elasticity) of the fabrics have been investigated. AFM has been used to measure the modulus of single nano fibril composite. Thermal conductivity has been measured precisely to study the effect of CNTs on thermal properties. Positron annihilation lifetime spectroscopy (PALS) was employed to measure the free volume properties of the fabrics and correlated it to fabric's morphological, mechanical and thermal properties. It has been noticed that in general the presence of CNTs decreased the free volume values resulted in dense structure and improved its thermal conductivity. Also, as CNTs diameter decreases the free volume decreases resulted in improvement in fabric's strength and thermal conductivity.

### Key Words:

Positron Annihilation; Mechanical Properties; Thermal Conductivity; SEM; TEM; AFM

-----  
*\*Corresponding Author:*

## 1. Introduction

Polymer nanofibers have been fabricated using an electrospinning process that produces nanofibers from an electrically charged jet of polymer solution. The nanofiber diameters range from 40 nm to 2 $\mu$ m, depending on the polymer types, bias voltage, viscosity of the solution, and so on [1]. One advantage of nanofibers is the high specific surface area developed by creating pores on the nanofiber surface [2]. Mechanical strength of an individual nanofiber is also expected to be enhanced with decreasing diameters [3]. This material has been widely applied to filters [4], scaffolds [5], protective clothing [6], and sensors [7]. Polyacrylonitrile (PAN) has been widely used to fabricate nanofibers owing to their easy carbonization process. PAN nanofiber fabrics can be used directly for electrode materials after stabilization and carbonization, which cannot be realized in other types of polymers. Another advantage of the carbonized PAN nanofiber is that; the nanofiber surface can be modified and functionalized by activation process under different ambient conditions [2]. G. Sui et al. [8] concluded that; the PP nanocomposite containing 5 wt. % CNF exhibits a high dielectric constant under wide sweep frequencies attended by low dielectric loss. Bal [9] showed an addition of 1 wt% of carbon nanofibers brought improvement in electrical properties of epoxy composite. Spitalsky et al. [10] studied nanotube/ polymer composites in which the presence of interconnected nanotube network results to a dramatic increase of their electrical conductivity. Also, nanocomposites based on Polymethylmethacrylate (PMMA) and MWCNTs as filler show a significant enhancement in the electrical conductivity. The multi wall carbon nanotubes (MWCNTs)/ PAN (20/80) Wt% composite papers without carbonization possess electrical conductivities of up to 0.5–1.0 S/cm at ambient temperature. However, the PAN-based carbon nanofibers are often required in many applications, which accompany inevitably stabilization and carbonization process. For instance, the PAN-based carbon nanofiber papers have been directly used for super capacitor electrodes, where high

capacitance of 173 F/g at 10mA/g was obtained but the power density was poor due to large electrical resistivity of the PAN-based carbon nanofibers [11]. Higher electrical conductivity is always desired to have high capacitance and high power density in super capacitors [12]. This is the main reason to introduce CNTs in PAN nanofibers. While CNT/ PAN nanofibers were prepared in organic solvent, CNT/polyethylene oxide (PEO) was electrospun in water with additional surfactant [13]. Dielectric properties vary with the compositions of iron (III) chloride dopant [14]. The permittivity behavior of the device at the frequency below 102 Hz shows the relaxation contribution along with the electrode polarization. Dielectric loss peak in loss tangent also confirms the presence of relaxing dipoles in TNFs. The AC conductance as a function of frequency confirms the semiconducting nature of TNFs and obeys Jonscher's power law except a small deviation in the low frequency region. DC conductivity increases with increase in temperature [15]. Ali [16-20] published a series of publications studying the characteristics of the electrospun PAN/DMF polymer solution in both wet and dry collectors before and after heat treatment as well as with and without nano reinforcements. Positron annihilation Lifetime spectroscopy (PALS) is an important method for measuring the change in properties of structural defects in many solids [21, 22]. In PALS, when a positron emitted from a positron source and injected in a polymer sample, it undergoes several processes (scatter and thermalize in the sample within a time of the order of 10 ps). The positron may eventually annihilate with an electron (free positron annihilation) or may extract an electron from the surrounding material to form a positronium atom (Ps). Ps is formed in two states; a singlet state (p-Ps) with anti-parallel spins has an intrinsic lifetime of 0.125 ns and a triplet state (o-Ps) with parallel spins has an intrinsic lifetime  $> 0.5$ ns. In o-Ps, the positron can annihilate with an electron from the surrounded atom by pick off annihilation and emit three photons. The pick off lifetime is directly related to the size of the free volume in a polymer.

Therefore, PALS has been used to characterize the properties of free volume of polymer nanocomposites, such as free-volume hole size, concentration, and its distribution [23- 26].

The present study is an attempt to study the effect of CNTs size and weight % on morphological and thermal properties of electrospun and treated (hot-pressed) CNTs/carbon flexible nano fibril fabrics as well as to correlate the presence of CNTs in the fabric's morphological and thermal properties to its intermolecular distances and free volume by using positron annihilation technique.

## **2. Experimental Work**

### **2.1. Materials**

Three different sizes of CNTs from Aldrich of the following numbering and dimensions; CNT#1: O.D. =10-30 nm, I.D.= 3-10 nm, L=1-10  $\mu$ m, CNT#2: O.D.= 30-50 nm, I.D.= 5-15 nm, L= 0.5-200  $\mu$ m, and CNT#3: O.D.= 40-60 nm, I.D.= 5-10 nm, L= 0.5-500  $\mu$ m. have been well dispersed by 24 sonication hours within five different weight concentrations from 1% to 5% in Dimethylformamide (DMF) solvent and then Polyacrylonitrile (PAN) of 150000 g/mol molecular weight from Aldrich catalog no. (181315) has been added with 10wt% then whole polymer solution and dispersions have been hot stirred at 60°C for 3 hours to ensure a complete PAN solubility.

### **2.2. Electrospinning of Dispersed CNTs/PAN nano fibril composites**

Electrospinning set-up assembled at NTC, Faculty of Engineering, Zagazig University, Egypt was used through the following steps; the PAN/DMF+MWCNTs polymer solution and dispersions were poured to fill a clean syringe of 10 ml volume. The syringe was connected to a metal tube of orifice inner diameter 0.9 mm. The metal tube was connected to the power supply at 25kV of positive potential. A metal screen collector of 15x15 cm dimensions was centered vertically at a 20 cm distance away from the orifice of the metal tube and covered with aluminum foil. The electrospun fibers were collected for about 16 hours to reach to collect CNTs/PAN nano fibril composite fabrics.

### **2.3. Production of Carbonized Fabrics**

About 2 cm from each side of the collected fiber mat was trimmed then the mat was placed in between two aluminum plates of 120x120 mm dimensions and 10 mm thickness after being covered with aluminum foil. The mold with the fabric in between was placed in a hot-press set to reach 220 °C with no applying pressure for 1 hour until the plate's temperature reached the maximum set temperature. Then 1 metric ton was applied for another one hour. The hot-

press was then allowed to cool down for another 1 hour while keeping the pressure on until it reaches  $100^{\circ}\text{C}$  then the pressure was released completely from the fabric except the weight of the upper aluminum plate until it has cooled down to room temperature. This process stabilized the PAN structure by adding an oxygen atom to PAN structure as well as activating the high surface energy accompanied with the nanofibril composites and use it as a cohesive bond to produce firm and uniform white fabrics. SEM and Raman investigations for such white fabrics have been conducted. Then, another hot-pressing for 3-hour in between single plate and double aluminum foils with 5 metric tons at  $380^{\circ}\text{C}$  has been applied then the pressure has been released after cool down to  $100^{\circ}\text{C}$ . This technique allowed to cyclize the carbon double bond and form graphitic hexagon structure from PAN. Reddish flexible and strong fabrics have been produced. Morphological, Chemical, Electrical, Thermal and Positron annihilation characterizations for the reddish sixteen fabrics has been conducted.

## **2.4. Characterization**

### **2.4.1. Electron Microscopy**

Scanning Electron Microscopy (SEM, JEOL JSM-5600LV) in the Central Laboratory for Elemental and Isotopic Analysis (Atomic Energy Authority Nuclear Research Center, Egypt) was used to characterize the fiber morphology, average diameter and its distribution of the both resultant white and reddish fabrics. High Resolution Transmission Electron Microscopy (HRTEM) (JEOL model JEM 2100) in Petroleum research Institute, Egypt) was used to investigate the morphologies of the fibers and the presence of CNTs in the resulting reddish fabrics.

### **2.4.2. Thermal Properties Measurements**

A thermal device at physics department, Faculty of Science, Tanta University, Egypt has been used at room temperature to measure the thermal conductivity and coefficient of thermal expansion.

### **2.4.3. Mechanical properties Measurements**

An optical extensometer attached to UTM has been used to measure the strength and modulus of the fabrics. Also AFM has been employed to measure the modulus of single nanofibril CNTs/carbon hybrid.

### **2.4.4. Positron Annihilation Spectrometer Measurements**

A conventional fast-fast coincidence spectrometer (ORTEC) with a time resolution 395 ps was used for PALS measurements [27], and the  $^{22}\text{Na}$  isotope with 10  $\mu\text{Ci}$  activity was used

as a positron source. This source was prepared using a droplet of  $^{22}\text{NaCl}$  solution dried onto two identical Kapton foils (7.6  $\mu\text{m}$  thick), which were afterward glued by epoxy glue, placed between two identical samples. The measured PAL spectra were fitted by LT computer program of Kansy [28]. The measurements carried out in air at room temperature. 1-2 million counts were accumulated for each spectrum. Only results with FIT values with deviation range from 1.05 up to  $\sim 1.2$  were considered as optimal ones. After source correction, each lifetime spectrum of the investigated samples was resolved into three lifetime components ( $\tau_1, \tau_2, \tau_3$ ) and their relative intensities ( $I_1, I_2, I_3$ ) respectively. The  $\tau_1$  is attributed to the para-positronium (p-Ps) annihilation. The  $\tau_2$  is attributed to the annihilation of positrons or positronium in defect of the ordered structure. The long-lived lifetime component  $\tau_3$  is attributed to the ortho-positronium (o-Ps) pick-off process in free volume holes in polymers. It directly correlates with the size of the free volume holes. A quantitative correlation between o-Ps lifetime  $\tau_3$  and the mean radius of holes  $R$  in a spherical geometry is known as Tao-Eldrup equation [29, 30]:

$$\tau_3 = 0.5 \left[ 1 - \left( \frac{R}{R_0} \right) + (1/2\pi) \text{Sin} \left( \frac{2\pi R}{R_0} \right) \right]^{-1} \quad (1)$$


Where:  $\tau_3$  and  $R$ , are expressed in ns and  $\text{\AA}$ , respectively,  $R_0=R+\Delta R$ ,  $\Delta R$  is the fitted empirical electron layer thickness (1.66  $\text{\AA}$ ). The average radius of the free volume hole  $R$  is related to the mean free volume,  $V_f$  (in  $\text{\AA}^3$ ) by a simple relation [31, 32]:

$$V_f = (4/3) \pi R^3 \quad (2)$$


### 3. Results and Discussion

#### 3.1. SEM and HRTEM characterization

SEM image Fig. 1 show the fiber morphological characterization and distribution of CNTs/Carbon nano fibril composites pattern for the 5 wt% CNT#1/Carbon reddish fabric. About 130 nm  $\pm$  32 nm average fibril diameter has been reported. HRTEM image (Fig. 2) shows CNT#1 bundle with diameter ranged from 6 to 16 nm wrapped by carbon nano fibers and aligned along the fiber axis.

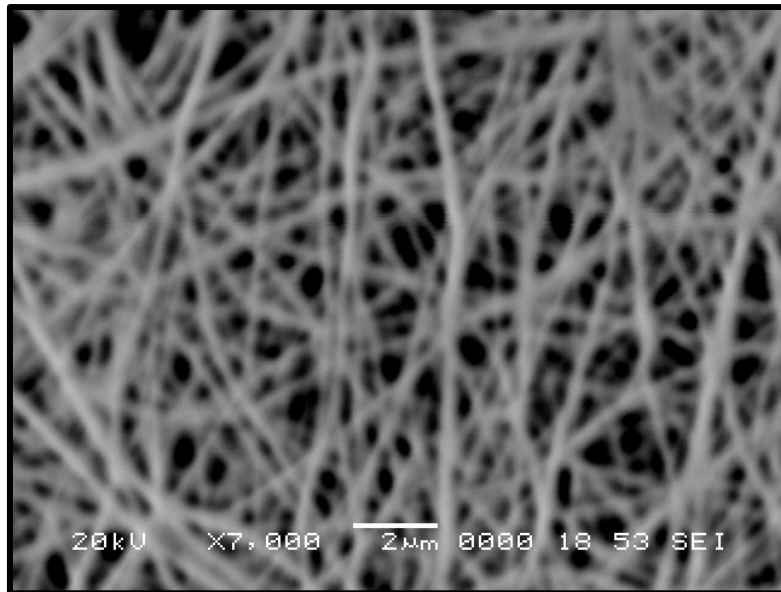


**Fig. 1:** SEM micrograph of CNTs/Carbon Reddish Fabrics

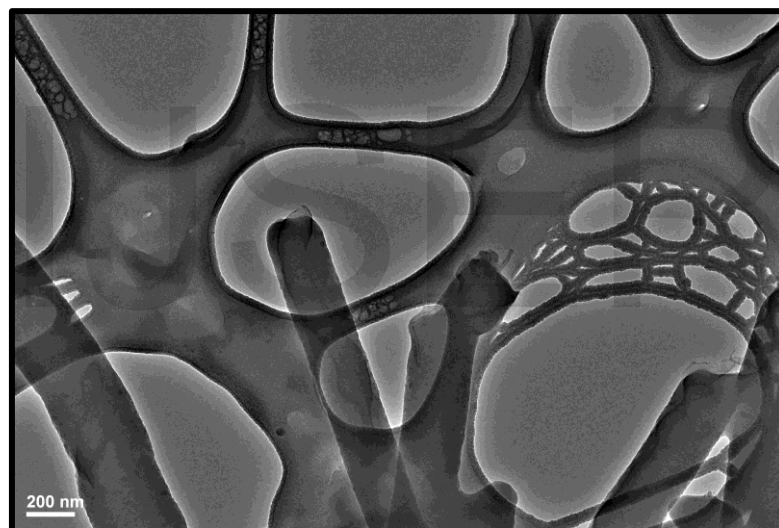

**Fig. 2:** HRTEM micrograph of CNTs/ Carbon Reddish Fabrics

### 3.3. Thermal Analysis

The effect of CNTs weight % in thermal properties of the fabrics have been measured and presented as shown in Figure (3)

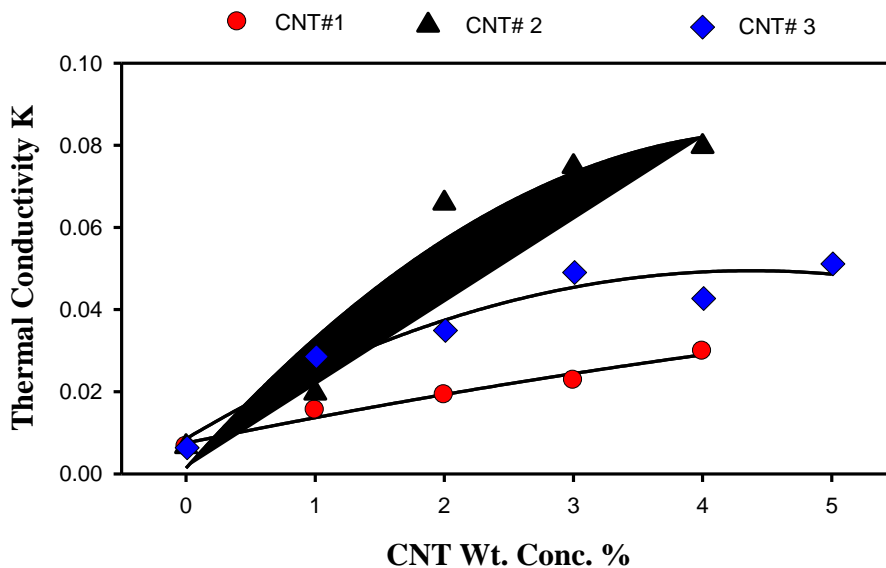

**Fig. 3:** CNT wt% vs. Thermal Conductivity

### 3.3 Mechanical Testing Analysis

Figure 4 represents the strengths value of all CNTs wt.% for all three sizes. It is obvious from the figure that as CNTs size increases in diameter and became close and compatible with the carbon fiber diameter a better strength values reported. On the other hand, as shown in Figure 5 the calculated values of modulus from stress-strain Fabrics results after it has been corrected by using optical extensometer showed same behavior and effect for CNTs sizes. Figure 6 represents the measurements of single fibril composite modulus by using AFM for 5wt% samples and it goes as the same of size compatibility between CNTs and carbon nano fiber.



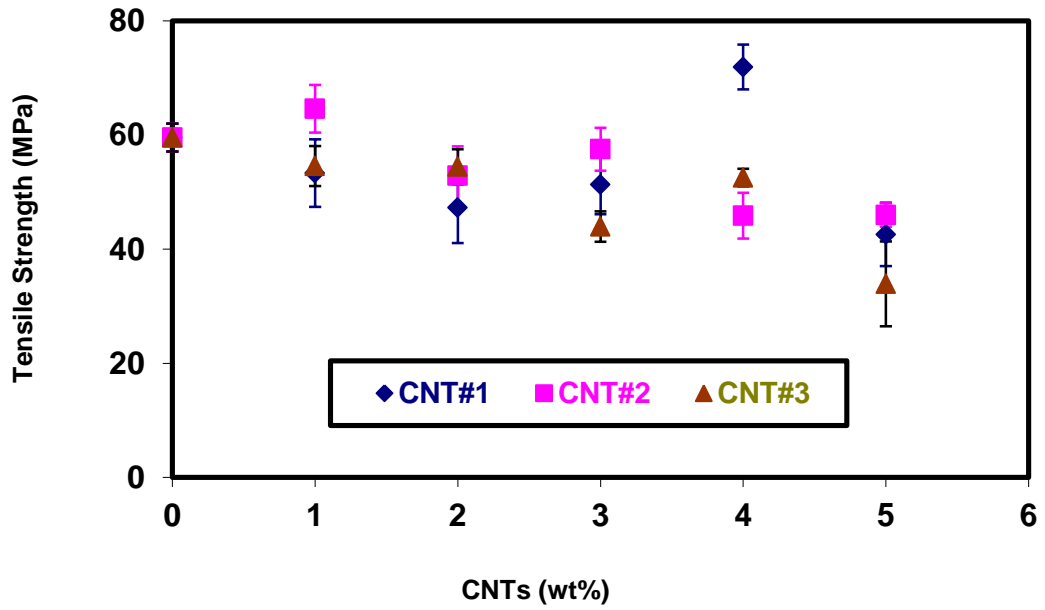


Fig. 4: Tensile strength vs. CNTs wt.% and size

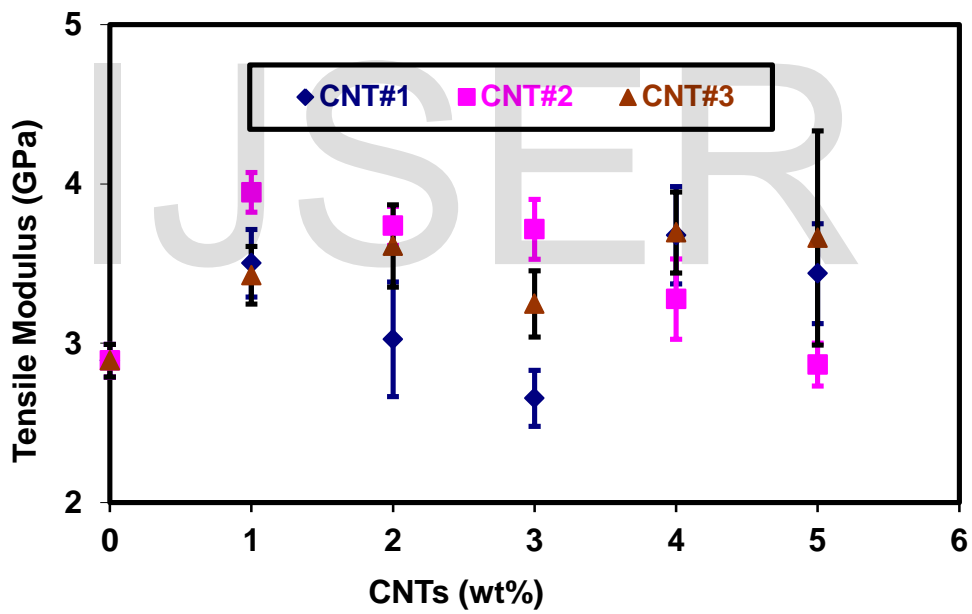


Fig. 5: Fabrics tensile modulus vs. CNTs wt.% and size

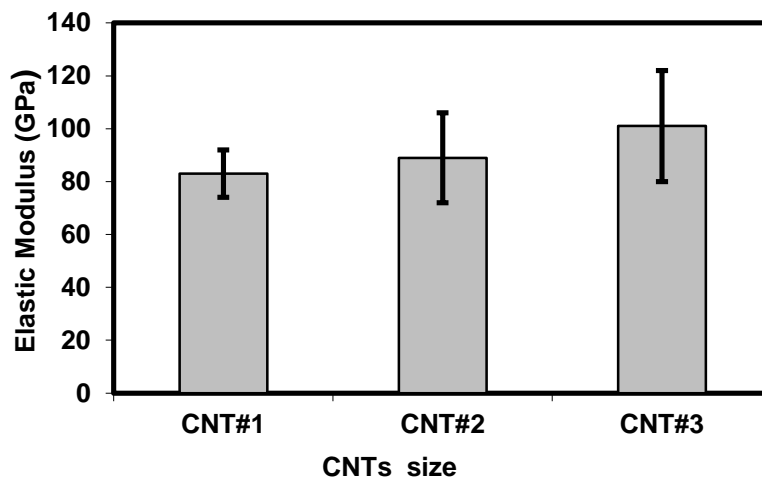



Fig.6: Single nano fibril composite tensile modulus vs. CNTs size

### 3.4. Positron Annihilation Analysis

The measured positron lifetime spectra for Carbon nano tubes (CNTs) of three different diameters, and each with five different weight concentrations were resolved into three lifetime components. These components are attributed to various states of positron annihilation. The first lifetime component  $\tau_1$  (fixed to 0.125 ns) and with intensity  $I_1$  ( $I_1 = 57-73\%$ ) is attributed to p-Ps. The intermediate component  $\tau_2$  (0.376- 0.486 ns) with its intensity  $I_2$  ( $I_2 = 23-37.5\%$ ) is related to annihilation of positrons without forming Ps, i.e., free positron annihilation. The longest lifetime component  $\tau_3$  ( $\tau_3 = (1.77-2.2\text{ ns})$ ) with its intensity  $I_3$  ( $I_3 = 3.4-5.9\%$ ) is due to the pick-off annihilation of o-Ps in the free volume sites present in the amorphous regions of the polymer matrix [33]. These two parameters  $\tau_3$  with intensity  $I_3$  are important and are of interest in this investigation, because  $\tau_3$  is related to the average free volume size and  $I_3$  is related to the relative number density of free volume holes. The average lifetimes ( $\tau_2, \tau_3$ ) and the relative intensities ( $I_1, I_2, I_3$ ) values measured for CNT#1, CNT#2 and CNT#3 are listed in Table 1. As illustrated in Table 1, the o-Ps lifetime components,  $\tau_3$ , with different CNTs concentration % does not have a systematic change with changing CNTs concentration. This is may be due to CNTs presence effect. On the other hand,  $I_3$ , the o-Ps probability formation also does not change systematically. This may be interpreted as  $I_3$  depends on chemical and physical properties of the nanofibril composites, and the trend of change in  $I_3$  may be related to whether or not polymer chains are covalently bonded to the surface of the nanotubes.

**Table 1:** The calculated values of Positron annihilation lifetime components with their corresponding intensities for the Carbon nanotubes (CNTs) of three different diameters

	Wt. %	$\tau_2$	$\tau_3$	$I_1$	$I_2$	$I_3$
<b>CNT #</b>		0.405±0.007	2.034±0.0330	69.2±0.71	26.9±0.7200	3.90±0.1
<b>CNT#1</b>	1%	0.376±0.002	2.009±0.017	66.28±0.13	29.94±0.13	3.784±0.038
	2%	0.410±0.007	2.236±0.035	67.15±0.46	28.13±0.47	4.72±0.100
	3%	0.417±0.006	1.969±0.038	66.17±0.41	29.82±0.41	4.01±0.120
	4%	0.402±0.004	2.137±0.025	73.20±0.24	23.38±0.23	3.42±0.052
	5%	0.433±0.007	2.040±0.023	70.67±0.67	25.24±0.69	4.09±0.079
<b>CNT#2</b>	1%	0.4474±0.007	2.023±0.04	70.22±0.67	26.08±0.68	3.70±0.12
	2%	0.4299±0.006	1.991±0.022	67.89±0.64	28.03±0.65	4.08±0.085
	3%	0.4206±0.0035	2.026±0.02	63.92±0.49	30.60±0.51	5.48±0.068
	4%	0.4865±0.0086	1.864±0.034	72.85±0.65	23.15±0.66	4.00±0.12
	5%	0.4640±0.010	2.000±0.038	70.48±0.65	24.85±0.66	4.66±0.14
<b>CNT#3</b>	1%	0.428±0.007	1.868±0.028	60.57±0.40	33.51±0.39	5.92±0.1
	2%	0.433±0.002	1.864±0.025	67.37±0.37	28.19±0.38	4.44±0.16
	3%	0.418±0.005	1.775±0.020	57.22±0.64	37.47±0.64	5.31±0.09
	4%	0.431±0.007	1.953±0.025	68.59±0.62	27.25±0.63	4.16±0.12
	5%	0.390±0.001	1.975±0.013	64.93±0.29	31.16±0.29	3.91±0.04

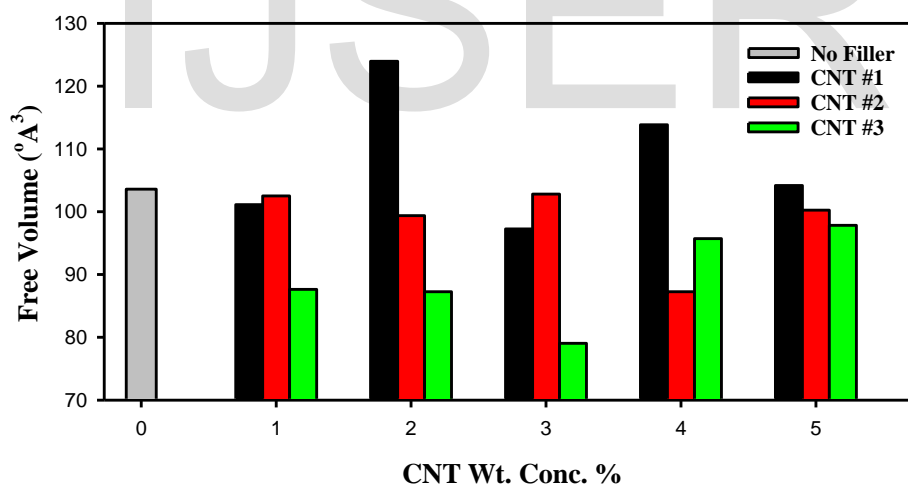

**Fig. 7:** Mean free volume ( $\text{\AA}^3$ ) as a function of filler concentration in Carbon nanotubes (CNTs) of three different diameters

The volume  $V$  ( $\text{\AA}^3$ ) of free volume nanoholes is calculated according to eqn. (2), where  $R$  is radius of the nano-holes calculated through eqn. (1). The variation of  $V$  ( $\text{\AA}^3$ ) as a function of CNTs concentrations of three different diameters are shown in Fig 7. The results showed that the average size of free volume for CNT#1, CNT#2 and CNT#3 are  $108 \pm 10.8$  ( $\text{\AA}^3$ ),  $98.4 \pm 6.4$  ( $\text{\AA}^3$ ) and  $89.5 \pm 7.5$  ( $\text{\AA}^3$ ) respectively. It can be noted that with increasing the average size of CNTs leads to decrease the average size of free volume. The obtained results

of o-ps lifetime  $\tau_3$  and consequently the average size of free volume are in a good agreement with that reported in the literatures [34]. Other studies showed that ortho-positronium principally annihilates from interfacial regions of polymer and nanotubes in the nanocomposite [35]. The increase of the average size of CNTs leads to an increase of the external surface area as well as the interstitial region volume among the CNTs and decreased free volumes at the fibres interface in the fabrics.

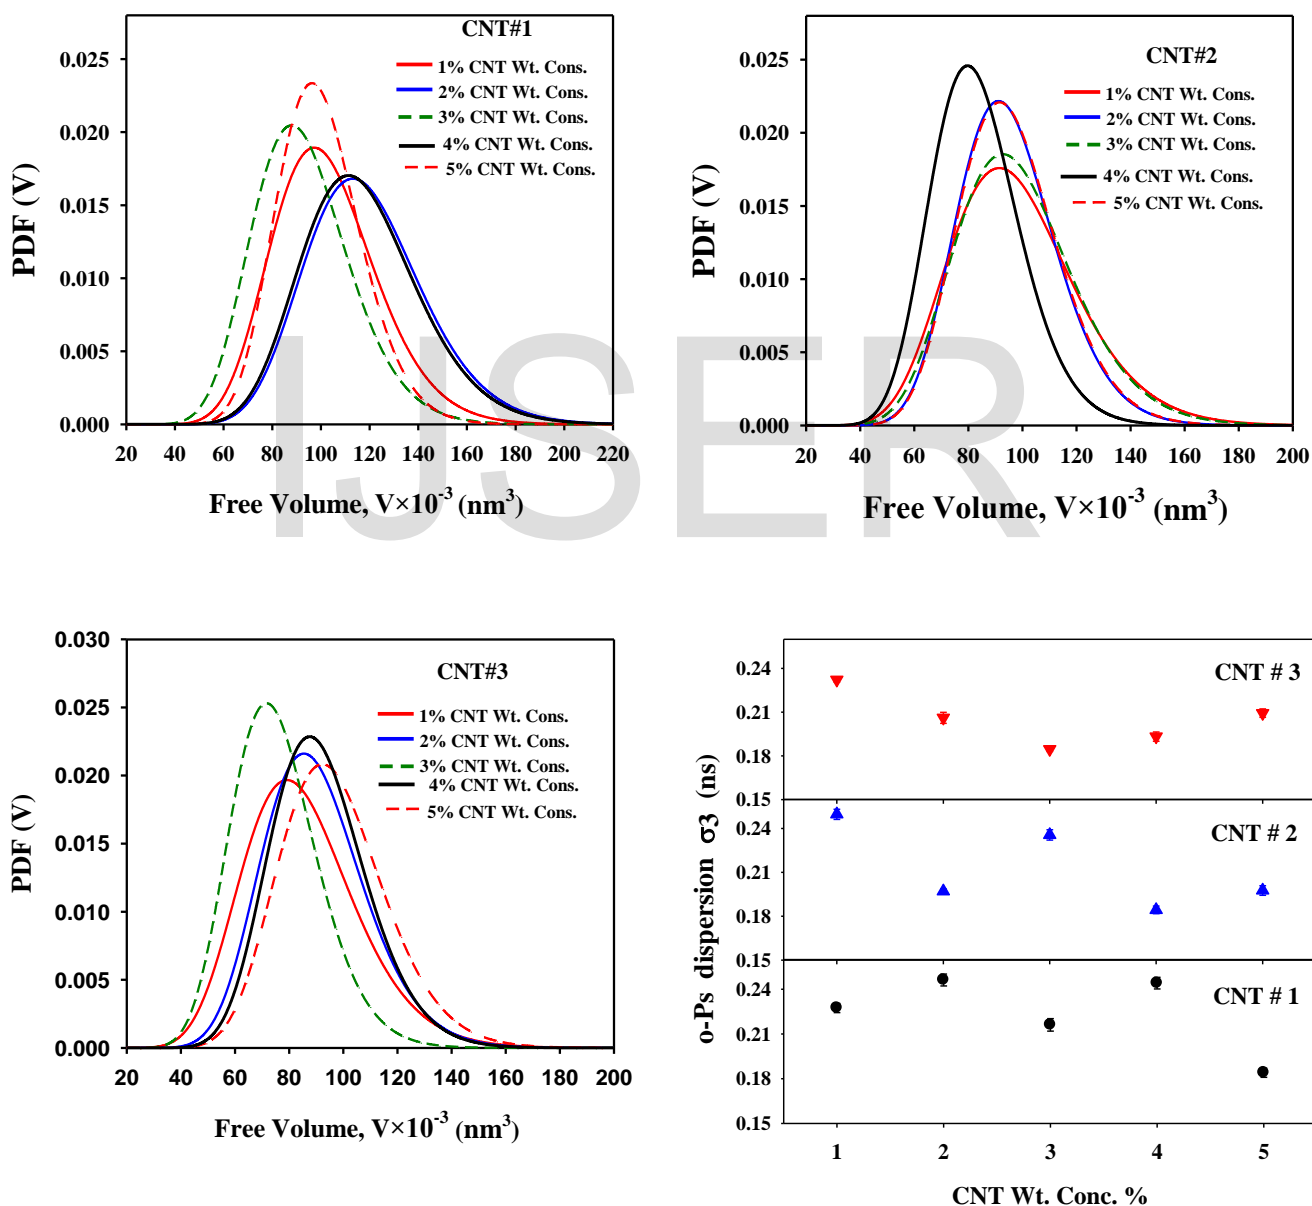


Fig.8: o-Ps lifetime distributions and its dispersion in different CNTs concentrations %

The LT program of Kansy [28] is used to fit the obtained positron annihilation lifetime data into free volume distributions based on the Tao–Eldrup equation (1). Figure 8 shows the distribution of free volume size,  $V$  ( $\text{nm}^3$ ) as a function of free volume nano holes ( $\text{nm}^3$ ) as well as lifetime dispersion  $\sigma_3$  from LT analysis for all the CNTs measured samples. It is interesting to observe that the average lifetime components of o-Ps and their intensities from continuous distributions were in good agreement with the discrete component analysis. Sharma et al. [35] have reported similar results for PF–CNTs composites. They showed that the peak position of the distribution shifts to a higher value with incorporation of CNTs, which is consistent with discrete component analysis. From the free volume hole size distributions, Figure 8, the calculated values of the full width at half maximum (FWHM) for the Carbon nanotubes (CNTs) of three different diameters are listed in Table 2. The results showed that in the case of CNT#1 and CNT#2 there are not systematic changes of the values of FWHM. In the case of CNT#3, the values of FWHM, Table 2, are decreased up to 3% CNTs concentrations indicating that the free volume size distribution becomes narrower with increasing the percentage of CNTs concentrations. The reduction in full width at half maxima with increasing the CNTs weight concentration% indicates that the nanotubes can lead to variation in packing density of chains in the vicinity of nanotubes, creating large size interfaces with the “annihilation” of smaller size nanoholes in the interphase region. A broader distribution of free volume size at a higher values  $> 3\%$  CNTs weight concentration is observed, indicating the presence of larger interfaces as a result of agglomeration of CNTs in the polymer matrix.

**Table 2:** The calculated values of the full width at half maximum (FWHM) for the Carbon nanotubes (CNTs) of three different diameters

CNTs Wt. conc. %	CNT#1	CNT#2	CNT#3
	FWHM ( $\text{nm}^3$ )	FWHM ( $\text{nm}^3$ )	FWHM ( $\text{nm}^3$ )
1%	0.044	0.048	0.042
2%	0.050	0.038	0.038
3%	0.040	0.044	0.032
4%	0.048	0.032	0.036
5%	0.036	0.036	0.040

## 4. Conclusions

Conclusions can be summarized as following:

1. As CNTs size is compatible in size with carbon nano fiber diameter a better fabrics mechanical and thermal properties have been reported.
2. Single nano fibril composites showed better modulus for CNTs#3 of lower free volume
3. Positron annihilation measurements indicated better mechanical and thermal properties are much correlated to fabrics minimum free volume values.

## Acknowledgements

Authors would like to thank Physics lab, Tanta University for allowing free thermal characterization of the samples.

## References

- [1] D. H. Reneker and I. Chun, Nanometre diameter fibres of polymer, produced by electrospinning, *Nanotechnology*, 7: 216-223, 1996.
- [2] W.J. Li, C.T. Laurencin, E.J. Caterson, R.S. Tuan, F.K. Ko, Electrospun nanofibrous structure: a novel scaffold for tissue engineering, *J Biomed Mater Res*, 60 (4): 613–621, 2002.
- [3] I.K. Kwon, S. Kidoaki, T. Matsuda, Electrospun nano- to microfiber fabrics made of biodegradable copolyesters: structural characteristics, mechanical properties and cell adhesion potential, *Biomaterials*, 26: 3929, 2005.
- [4] P.P. Tsai, H. Schreuder-Gibson, P. Gibson, Different Electrostatic Methods for Making Electret Filters, *J. Electrostat.*, 54:333, 2004.
- [5] A. Fertala, W.B. Han, F.K. Ko, Mapping critical sites in collagen II for rational design of geneengineered proteins for cell-supporting materials, *J. Biomed. Mater*, 57: 48, 2001.
- [6] P.W. Gibson, H.L. Schreuder-Gibson, D. Rivin, Electrospun Fiber Mats: Transport properties, *AIChE J.*, 45:190, 1999.
- [7] B. Ding, J. Kim, Y. Miyazaki, S. Shiratori, Electrospun nanofibrous membranes coated quartz crystal microbalance as gas sensor for NH<sub>3</sub> detection, *Sens. Actuat., B* 101: 373–380, 2004.
- [8] G. Sui, S. Jana, W.H. Zhong , M.A. Fuqua, C.A. Ulven, Dielectric properties and conductivity of carbon nanofiber/semi-crystalline polymer composites, *Acta Materialia*, 56:2381–2388, 2008.
- [9] Bal S, Experimental study of mechanical and electrical properties of carbon nanofiber/epoxy composites, *Mater Design*, 31:2406–2413

- [10] Spitalsky Z, Tasis D, Konstantinos Papagelis K, Galiotis C, Carbon nanotube-polymer composites, *Chem Process Mech Electr Prop*, 35:357–401, 2010.
- [11] C. Kim, K.S. Yang, Electrochemical properties of carbon nanofiber web as an electrode for super capacitor prepared by electrospinning, *Appl. Phys. Lett.*, 83:1216, 2003.
- [12] A.B. Dalton, S. Collins, E. Munoz, J.M. Razal, V.H. Ebron, J.P. Ferraris, J.N. Coleman, B.G. Kim, R.H. Baughman, Super-tough carbon-nanotube fibres, *Nature*, 423 (12): 703, 2003.
- [13] Y. Dror, W. Salalha, R.L. Khalfin, Y. Cohen, A.L. Yarin, E. Zussman, Carbon nanotubes embedded in oriented polymer nanofibers by electrospinning, *Langmuir*, 19:7012, 2003.
- [14] Mohd Hamzah Harun, Elias Saion, Anuar Kassim, Ekramul Mahmud, Muhd Yousuf Hussain, and Iskandar Shahrim Mustafa” Dielectric Properties of Poly (vinyl alcohol)/Polypyrrole Composite Polymer Films, *JOURNAL FOR THE ADVANCEMENT OF SCIENCE & ARTS*, VOL. 1: NO. 1, Jan-June 2009.
- [15] S.S. Batool, Z.Imran, M.A.Rafiq, M.M.Hasan, M.Willander, Investigation of dielectric relaxation behavior of electrospun titanium dioxide nanofibers using temperature dependent impedance spectroscopy, <http://dx.doi.org/10.1016/j.ceramint.08.024>, 2012.
- [16] Ali AA, Wet electrospun nanofibers, *Al-Azhar Engineering Eights International Conference*, Egypt, December 24-27, 2004.
- [17] Ali AA and El-Hamid M, Electrospinning optimization for precursor carbon nanofiber, *Composites A*, 37:1681-1687, 2006.
- [18] Ali AA, Self-assembled ultra-fine carbon coils by wet electrospinning, *materials letters*, 60:2858-2862, 2006.
- [19] Ali AA and Rutledge GC, Hot-pressed electrospun PAN nanofibers, An idea for flexible carbon mat, *Journal of materials processing technology*, 209:4617-4620, 2009.
- [20] Ali AA and Al-Asmari A Kh, Wet-electrospun CuNP/carbon nano fiber composites: potential application for surface mounted component, *Applied Nanoscience*, 2:55-61, 2012.
- [21] Y. C. Jean, P. E. Mallon and D. M. Schrader. Principles and Applications of Positron & Positronium Chemistry. (World Scientific Publishing Co. Pte. Ltd., New Jersey, 2003.
- [22] A. Dupasquier and Jr. A. P. Mills. Positron Spectroscopy of Solids. (IOS Press, Amsterdam and SIF, Bologna, 1995.
- [23] J. Zhang, M. Yang and F. H. J. Maurer, *Macromolecules*, 2011, 44, 5711.
- [24] S. Harms, K. Ratzke, F. F. Gerald, J. Schneider, L. Willner and D. Richter, *Macromolecules*, 43, 10505, 2010.
- [25] R. Zaleski, A. Kierys, M. Grochowicz, M. Dziadosz and J. Goworek, *J. Colloid Interface Sci.*, 358, 268, 2011.
- [26] S. Awad, H. Chen, G. Chen, X. Gu, J. L. Lee, E. E. Abdel-Hady and Y. C. Jean, *Macromolecules*, 44, 29, 2011.

- [27] K. R. Mahmoud, S. Al-Sigeny, T. Sharshar, H. El-Hamshary, El-Hamshary: Positron annihilation study on free volume of amino acid modified, starch-grafted acrylamide copolymer, *Radiat. Phys. Chem.* 75: 590-595, 2006.
- [28] J. Kansy, Microcomputer program for analysis of positron annihilation lifetime spectra, *Nucl. Instrum. Meth. A*, 374: 235-244, 1996.
- [29] M. Eldrup, D. Lightbody, J. Sherwood, The temperature dependence of positron lifetimes in solid Pivalic acid. *Chem. Phys.*, 63, 51-58, 1981.
- [30] S. Tao, Positronium annihilation in molecular substances. *J. Chem. Phys.* 56, 5499-5510, 1972.
- [31] McGonigle, E.-A., Liggat, J.J., Pethrick, R.A., Jenkins, S.D., Daly, J.H., Hayward, D., Permeability of N<sub>2</sub>, Ar, He, O<sub>2</sub> and CO<sub>2</sub> through biaxially oriented polyester films dependence on free volume. *Polymer* 42, 2413-2426, 2001.
- [32] Porto, A.O., Goulart Silva, G., Magalhães, W.F., Free volume-size dependence on temperature and average molecular-weight in poly(ethylene oxide) determined by positron annihilation lifetime spectroscopy. *J. Polym. Sci.* 37, 219-226, 1999.
- [33] Thimmaraju Jeevananda, Nam Hoon Kim, Joong Hee Lee, Siddaramaiah Basavarajaiah, MV Deepa Urs and Chikkakuntappa Ranganathaiah, "Investigation of multi-walled carbon nanotube-reinforced high-density polyethylene/carbon black nanocomposites using electrical, DSC and positron lifetime spectroscopy techniques" *Polym Int* 58: 775-780, 2009.
- [34] Somia Awad, H. M. Chen, Brian P. Grady, Abhijit Paul, Warren T. Ford, L. James Lee and Y. C. Jean, " Positron Annihilation Spectroscopy of Polystyrene Filled with Carbon Nanomaterials" *Macromolecules* 45, 933-940, 2012.
- [35] S. K.Sharma , J.Prakash, K.Sudarshan, P.Maheshwari, D. Sathiyamoorthy and P. K. Pujari, "Effect of interfacial interaction on free volumes in phenol-formaldehyde resin-carbon nanotube composites: positron annihilation lifetime and age momentum correlation studies" *Phys. Chem. Chem. Phys.*, 14, 10972-10978, 2012.